

RESEARCH ARTICLE

## Evaluation antibacterial activity of Biosynthesized Silver Nanoparticles using e *Euphorbia Pseudocactus Berger* extracts (*Euphorbiaceae*)

Yasin Sadeghipour<sup>1</sup>, Mohammad Hassan Alipour<sup>2</sup>, Hamid Reza Ghaderi Jafarbeigloo<sup>3</sup>, Afsaneh Salahvarzi<sup>4</sup>, Mehdi Mirzaii<sup>5</sup>, Ali mohammad Amani<sup>1,6\*</sup>, Sareh Mosleh-shirazi<sup>7</sup>, Mohsen Mehrabi<sup>8</sup>

<sup>1</sup> Department of Medical Nanotechnology, School of Advanced Medical Sciences and Technologies, Shiraz University of Medical Sciences, Shiraz, Iran

<sup>2</sup> Social Security Organization, shahid beheshti hospital, shiraz, Iran

<sup>3</sup> Department of Basic Science, Payame Noor University, Iran

<sup>4</sup> Department of Chemistry and Nanochemistry, Faculty of Sciences & Modern Technologies

<sup>5</sup> Department of Medical Microbiology, School of Medicine, Shahrood University of Medical Sciences, Shahrood, Iran

<sup>6</sup> Pharmaceutical Sciences Research Center, Shiraz University of Medical Sciences, Shiraz, Iran

<sup>7</sup> Department of Material Engineering, Shiraz University of Technology, Shiraz, Iran

<sup>8</sup> Department of Medical Nanotechnology, School of Medicine, Shahrood University of Medical Sciences, Shahrood, Iran

### ARTICLE INFO

#### Article History:

Received 28 May 2020

Accepted 16 Jul 2020

Published 01 Aug 2020

#### Keywords:

silver nanoparticles

*Euphorbia Pseudocactus*

*Berger (Euphorbiaceae)*

antibacterial

molecular dynamics

### ABSTRACT

In the current research, silver nanoparticles (Ag NPs) were created using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) extracts, which played the main role in the formation and stability of nanoparticles. The physic-chemical properties of biosynthesized nanoparticles were characterized by means of Ultraviolet–Visible spectroscopy (UV-Vis), X-ray diffraction (XRD), and Transmission Electron Microscopy (TEM), and Fourier-Transform Infrared spectroscopy (FT-IR) methods. UV-Vis results illustrated that maximum plasma resonance absorption of Ag NPs are about 426 nm. Size distribution and spherical morphology was determined by TEM method. The XRD was confirmed face centered cubic (FCC) structure for synthesized nanoparticles. Monte Carlo (MC) simulations and Molecular dynamics (MD) were utilized to evaluate the nanoparticles. The antibacterial properties of biosynthesized Ag NPs were studied on *E. coli* (ATCC 25922), *S. aureus* (ATCC 2592), *P. aeruginosa* (ATCC27853) and *E. faecalis* (ATCC51299) using micro dilution broth method. The minimum inhibitory concentration (MIC) results of synthesized Ag NPs on *S. aureus* and *E. faecalis* obtained 4 and 8 µg/mL and *P. aeruginosa* and *E. coli* obtained 16 and 4 µg/mL. So, synthesized nanoparticles can be utilized as an antibacterial agent in medical and industrial devices and tools.

#### How to cite this article

Sadeghipour Y., Alipour MH., Ghaderi Jafarbeigloo HR., Salahvarzi A., Mirzaii M., Amani AM., Mosleh-shirazi S., Mehrabi M. Evaluation antibacterial activity of Biosynthesized Silver Nanoparticles using e *Euphorbia Pseudocactus Berger* extracts (*Euphorbiaceae*). *Nanomed Res J*, 2020; 5(3): 265-275. DOI: 10.22034/nmrj.2020.03.007

### INTRODUCTION

Silver nanoparticles considered the attention of researchers because of their electrical, opt-

ical, thermal and biological properties [1, 2]. These properties cause that they be suitable for applications in the fields such as drug delivery, sensing, antibacterial and catalysis [3-11].

\* Corresponding Author Email: [Aliamani1400@gmail.com](mailto:Aliamani1400@gmail.com)  
[Mosleh@sutech.ac.ir](mailto:Mosleh@sutech.ac.ir)

 This work is licensed under the Creative Commons Attribution 4.0 International License.

To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

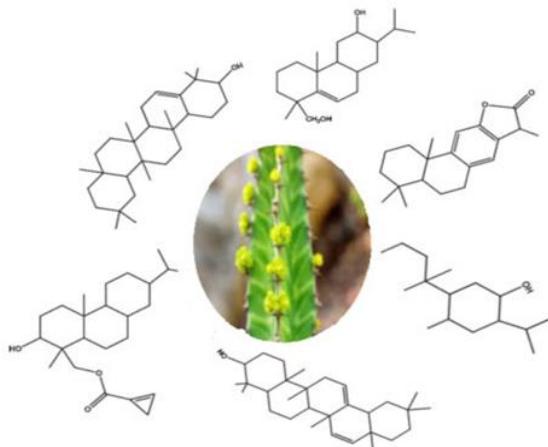


Fig. 1. shows the *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) plant and some of the compounds and functional groups involved in the synthesis and stability of silver nanoparticles[43].

It has been reported that the excessive usage of antibiotics to eradicate the bacteria resulted in the development of resistance to various antibiotics as well as the spread of infectious diseases [12-14]. Therefore, the find of new antibacterial agents is essential for the prevention of bactericidal growth. Silver nanoparticles have significant antibacterial activity, due to having small size and the surface: volume ratios of these particles. Therefore, owing to high antibacterial properties of these nanoparticles, they could be employed for the increase of the safety in the manufacturing such as food packaging [15, 16].

These nanoparticles prepare thought several physical and chemical methods such as gamma irradiation [17], electrical irradiation[18], thermal decomposition[19], and sol-gel[20]. But these methods require to long-term experiments, a large space, use of toxic chemicals, high energy and expensive[21, 22] . So, synthesis of nanoparticles using microorganisms[23-26], enzymes[27], and plant extracts is best choose, due to advantageous such as the short-term experiments, cost-effective, easily, available, and safe[28]. Leaves, barks, stems, seeds, flowers and roots are parts of plant which can be used as reducing and stabilizing agents for the construction of nanomaterials[29-33]. The compounds like terpenoids[34], flavonoids[35], phenols [36], saponins[37], polysaccharide [38], quinones [39] present in the plants cause the reduction of metal ions.

*Euphorbia Pseudocactus Berger* (*Euphorbiaceae*)  
*Euphorbia pseudocactus Berger* (candelabra

spurge) is a multibranched, dwarf-stemmed, candelabra-shaped, succulent herb, 60–120 cm tall. The stems often have distinctive yellow V-shaped markings. It is originating in the subtropical coast of South Africa. It grows in thorny bush-lands and savannah often forming colonies.

some species of *Euphorbia* are useful for the treatment of boils, cuts, and wounds[40]. It is useful for cardiovascular complaints, asthma, cough,[41] and spleen disorders[42]. Certain *Euphorbia* species have been reported to possess cytotoxic[43-47], antimicrobial[48-52], larvicidal, insecticidal[53], anti-inflammatory, hepatoprotective, and antioxidant activities [54-56]. The diterpenoid ingredients, particularly those with tigliane, ingenane, and abietane skeletons, are believed to be the major bioactive and toxic agents [57]. So, in this paper, we study the synthesis of silver nanoparticles by using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) extract and its antibacterial property.

## EXPERIMENTAL

### Materials and method

Fresh leaves of *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) were gathered from Jam, Bushehr, Iran. Silver nitrate ( $\text{AgNO}_3$ ) was procured from Merck. The gathered herb was cleansed by using distilled water, and was dried at ambient temperature. Then they were powdered and stored for done experimental.

### Extraction

Fresh *Euphorbia Pseudocactus Berger*

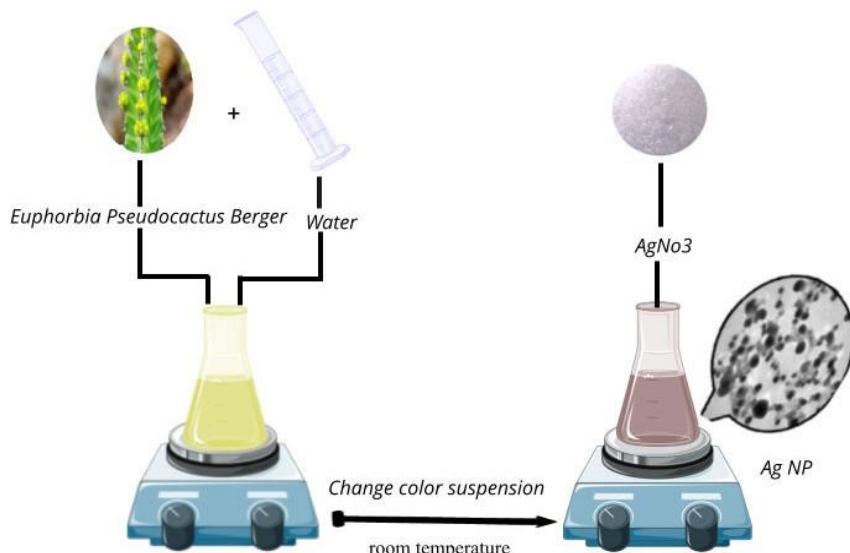


Fig. 2. shows the production of *Euphorbia Pseudocactus Berger* plant extract and discoloration of the plant extract with the addition of  $\text{AgNO}_3$  solution.

(*Euphorbiaceae*) extract was preferred to reduce aqueous  $\text{Ag}^+$  solution to Ag NPs. So, 5g powder plant was refluxed in 50 ml distilled water under stirred extremely for 2h. The resulting solution gradually cooled down at 25°C and then filtered using Whatman filter paper No. 1. Fresh extracts were employed for the preparation of Ag NPs.

#### Synthesis of Ag NPs

Typically, 20 ml fresh filtered extract was interacted with 5 ml aqueous 0.01 mM  $\text{AgNO}_3$  under reflux by magnetic stirred. After interaction for 30 min, color of suspension was converted from light-yellow to brown which this change illustrated formation of Ag NPs. The brown Ag suspension was cooled at room temperature, and it was identified by using several techniques (Fig. 2).

#### Characterization of Ag NPs

UV-Vis spectroscopy (UV-Vis) was performed through Varian Cary 50 UV-vis spectrophotometer. The X-ray diffraction (XRD) of samples was done on Holland-Philips X-ray powder diffractometer using Cu Ka radiation ( $= 0.1542 \text{ nm}$ ). TEM of synthesized nanoparticles was performed using Transmission Electron Microscopy model of CM30 3000Kv. FT-IR spectra was recorded through Bruker VERTEX 80 v model.

#### Microorganisms and growth conditions

The antimicrobial activity of the prepared Ag

NPs has tested through standard micro dilution technique-reveals the minimum inhibitory concentration (MIC), which MIC value is the lowest concentration of Ag NPs to inhibit bacterial growth up to 99%. To investigate of antibacterial effect of prepared Ag NPs was used several type of Gram-negative and Gram-positive bacteria. Gram-negative bacteria involved *Escherichia coli* (ATCC 25922) and *Pseudomonas aeruginosa* (ATCC 27852) and Gram-positive bacteria including *Staphylococcus aureus* (ATCC 25923) and *Enterococcus faecalis* (ATCC 27852). Cultivating bacteria was carried out on Mueller-Hinton agar (MHA) at 37 °C for 18-24 h.

#### Antibacterial Test

Antibacterial activity of synthesized nanoparticles was studied on standard species of bacteria including both gram-positive and gram-negative bacteria of *S. aureus*, *E. coli*, *E. faecalis*, *P. aeruginosa* by micro dilution broth method (M27-A3) documented by CLSI. In brief, for designation of antibacterial activity, serial dilutions of synthesized nanoparticles (0.5-128  $\mu\text{g}/\text{mL}$ ) were prepared in a 96-well micro-titer plate using Müller-Hinton broth (MHB, EMD Millipore) medium ( $\text{pH}=7 \pm 0.1$ ; 25°C) based on the M07-A10 protocol. Stock inoculums ready using transferring some pure colonies in 5 mL sterile DW and adjust the turbidity of the inoculums to 0.5McFarland standard at 530 nm wavelengths which are equal to

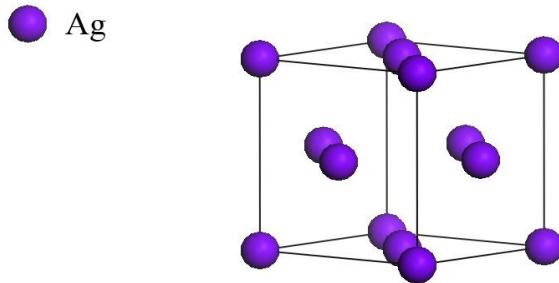


Fig. 3. Simulated crystal structure of Ag

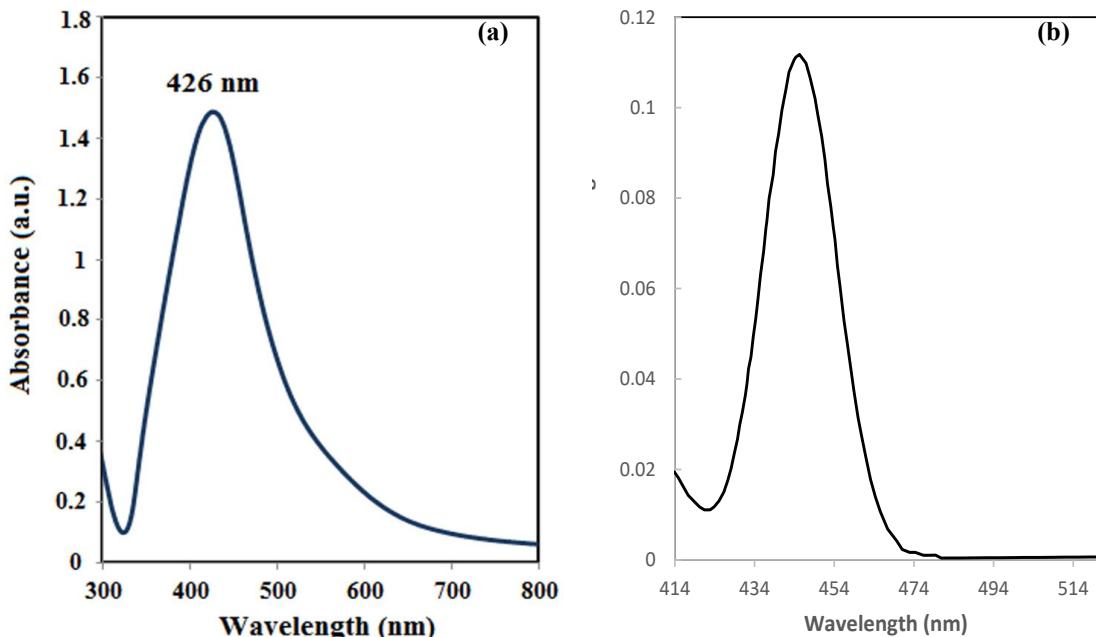


Fig. 4. UV-Vis spectrum of (a) biosynthesized Ag NPs *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) and (b) simulation result

1–1.5 × 10<sup>8</sup> cells/mL for bacteria. Working suspension was prepared by production a 1/100 dilution with Müller-Hinton broth to add wells. The one column of 96-well microplate was filled with 200 μL of MHB media culture as positive control. The other column was filled with 200 μL of bacterial suspension as negative control. The two other columns were filled with 100 μL inoculum and 100 μL of nanoparticles dilution sequentially. The growth of bacteria treated with nanoparticles was compared with those grown in the control group. The values of MIC were defined by the lowest concentrations of the reduction in the bacterial growth in comparison with the growth in the control group. The experiments were performed in triplicate.

#### Simulation details

In this work, both molecular dynamics (MD) and monte carlo (MC) simulations were done by Materials Studio v17.1.0.48 to simulate the XRD and UV-vis, respectively. To geometry optimization, universal force field, the atom based van der Waals, and Ewald Electrostatic were performed. The simulated structures of Ag is face centered cubic (FCC) with lattice parameters of 4.08 Å as shown in Fig. 3. UV-vis and XRD simulation can be evaluated using VAMP and diffraction module, respectively. Also, XRD pattern of Ag simulated investigate based on freely equilibrated configurations by Cu and Kα radiation ( $\lambda = 1.54 \text{ \AA}$ ).

Table 1. shows some UV-Vis spectrum of biosynthesized Ag NPs that have been synthesized using various plant extracts.

Plant	The absorption peak of UV-Vis spectrum	References
<i>Macrotyloma uniflorum</i>	410–430 nm	[58]
<i>macroalga Chaetomorpha linum</i>	422 nm	[59]
<i>Calendula officinalis</i>	440 nm	[60]
<i>Alternanthera sessilis (Linn.)</i>	435 nm	[61]
<i>Pithophora oedogonia (Mont.)</i>	445 nm	[62]
<i>RedApple (Malus domestica)</i>	409 - 448 nm	[63]
<i>Bunium persicum</i>	400 nm	[64]

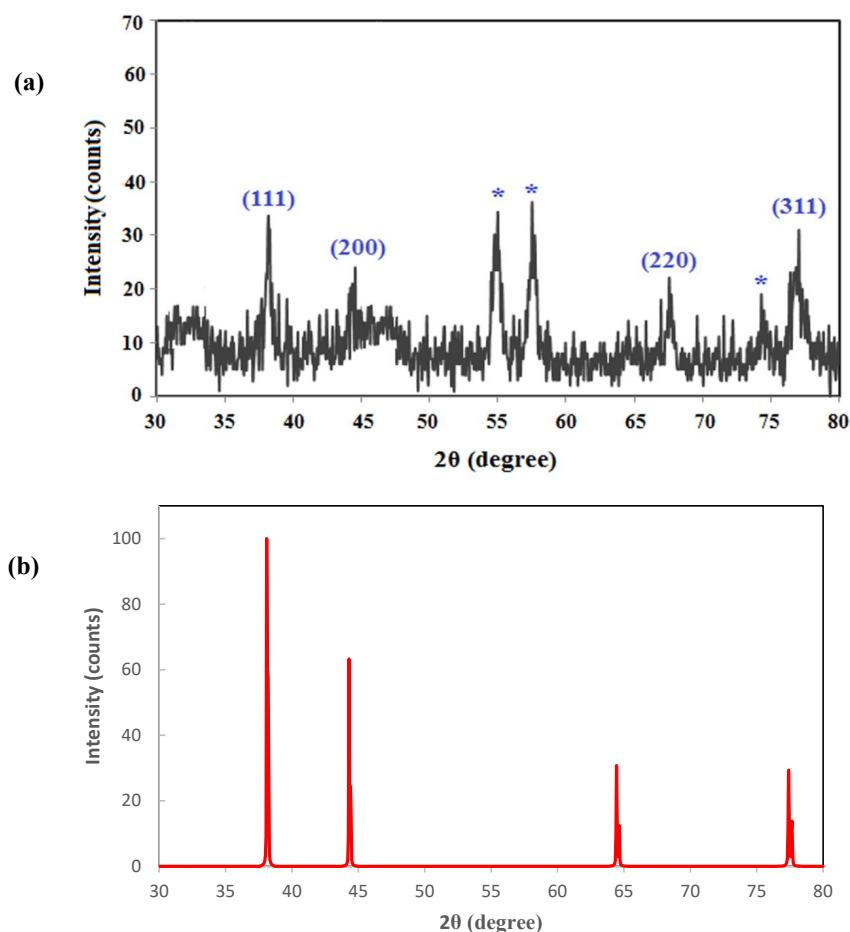


Fig. 5. (a) XRD pattern of biosynthesized Ag NPs, and (b) Simulated XRD pattern in molecular dynamics simulation for Ag NPs

## RESULTS AND DISCUSSION

UV-Vis Spectroscopy a quantitative technique applied to measure the optical absorption spectra of metal nanoparticles. Absorption spectrum shows that maximum plasmon resonance absorption of simulation result and biosynthesized Ag NPs is in region of 447 and 426 nm, respectively, which confirmed formation of of *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) (Fig. 4).

*Berger (Euphorbiaceae)* (Fig. 4).

X-ray diffraction pattern (XRD) of biosynthesized Ag NPs using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) presents in Fig. 5a. All of the peaks with Miller indices of (111), (200), (220) and (311) can be indexed to the face centered cubic (FCC) structure for biosynthesized nanoparticles (JCPDS, 04-0783). The crystalline

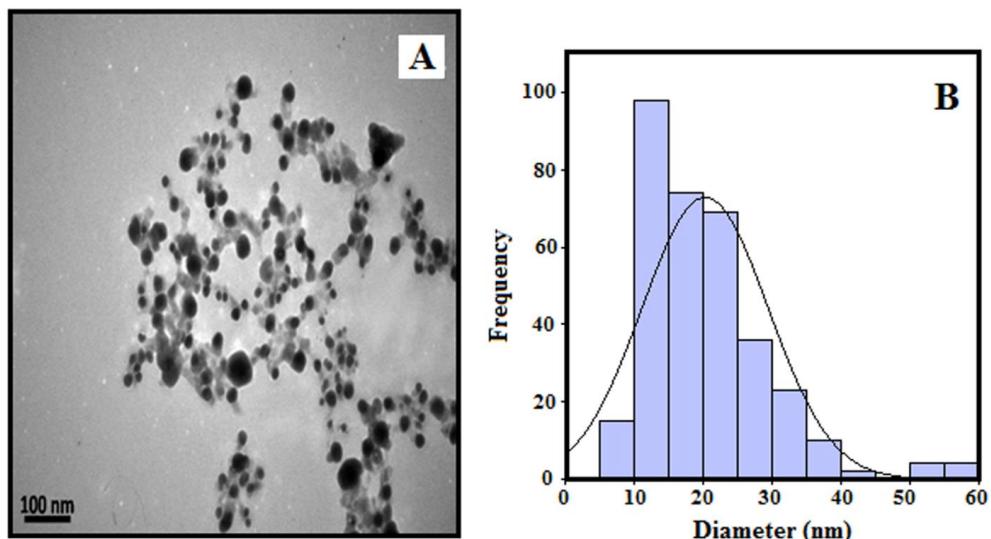


Fig. 6. (a) TEM image, (b) size distribution histogram of biosynthesized Ag NPs using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*)

Table 2. shows some of the different plants used to synthesize nanoparticles and their size and morphology compared to prepare Ag NPs in this study.

Plant	Type of NPs	Size (nm)	Morphology	References
<i>Musa balbisiana</i> (banana)	Silver	200 nm	triangles, pentagons and hexagons	[67]
<i>Boerhaavia diffusa</i>	Silver	25 nm	spherical	[68]
<i>Azadirachta indica</i>	Silver	34 nm	spherical	[69]
<i>Embelica officinalis</i> (EO)	Silver	15 nm	spherical	[70]
<i>Ziziphora tenuior</i> (Zt)	Silver	38 nm	spherical	[71]
<i>Pulicaria glutinosa</i>	Silver	40-60 nm	spherical	[72]
<i>Ananas comosus</i>	Silver	12 nm	spherical	[73]

size of Ag NPs evaluated using Scherrer's formula ( $D=0.9\lambda/\beta\cos\theta$ ; where  $\lambda$  is X-ray wavelength,  $\beta$  is full width at half the maximum (FWHM) and  $\theta$  is Braggs' angle) in about 42 nm [65]. Some extra peaks in XRD pattern related to bioorganic phases residue and impurities such as AgCl on surface of nanoparticles[66]. Simulated XRD pattern in molecular dynamics simulation for Ag is present in Fig. 5b. The peaks at  $2\theta=38.1^\circ$ ,  $44.3^\circ$ ,  $64.4^\circ$ , and  $77.4^\circ$  are close to experimental measurement.

Transmission Electron Microscopy (TEM) is a scientific instrument that applies a beam of highly energetic electrons to evaluate the morphology, particle size, and size distribution of nanoparticles. TEM micrograph of biosynthesized Ag NPs using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) extract shown in Fig. 6a. It clearly indicates that the biosynthesized Ag NPs are spherical shape and well dispersed. The histograms of particle distribution present in Fig. 6b. The biosynthesized Ag NPs have

size range from 5.48-60 nm with average diameter of about 9.16 -20.31 nm.

FT-IR spectral analysis of biosynthesized Ag NPs shows in Fig. 7. The main goal of FT-IR analysis is to detect the organic functional groups present in plant extract. The spectrum shows stretching vibrations as  $3500\text{ cm}^{-1}$  (N-H, amide),  $3472$  - $3413\text{ cm}^{-1}$  (O-H, alcohol and phenol),  $3231\text{ cm}^{-1}$  (O-H, carboxylic acid),  $2923$ - $2358\text{ cm}^{-1}$  (C-H, methyl, methylene, and methoxy),  $1640\text{ cm}^{-1}$  and  $1618\text{ cm}^{-1}$  (C=O, carboxylic acid),  $1383\text{ cm}^{-1}$ (C-H, alkanes),  $1111\text{ cm}^{-1}$  (C-OH, disaccharides), and  $620\text{ cm}^{-1}$  (aromatic ring, carbohydrates).

Thus, FT-IR spectral showed that compounds and functional groups such as: amide, alcohol, phenol, carboxylic acid, methyl, methylene, methoxy, carboxylic acid, alkanes, disaccharides, aromatic ring and carbohydrates play significant roles in the, reduction, stabilization, and formation of these silver nanoparticles.

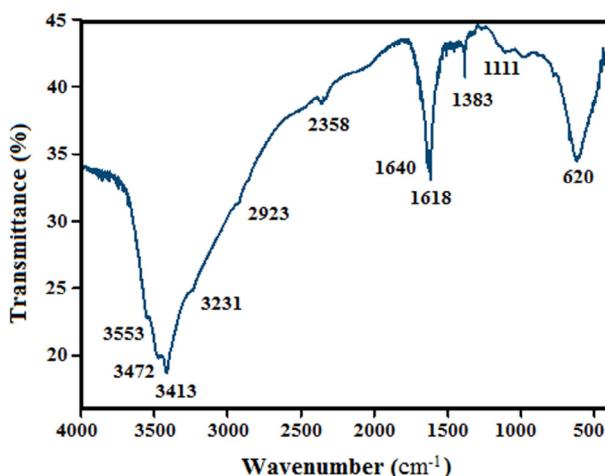
Fig. 7. FT-IR spectrum of biosynthesized Ag NPs using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) extract

Table 3. shows some of the most effective compounds and functional groups in plant extracts that play an important role in the formation, reduction, stabilization, and capping of nanoparticles.

Plant	Type of NPS	effective compounds and functional groups	References
<i>Jatropha curcas</i>	Silver	curcain (an enzyme), curcacycline A (a cyclic octapeptide), curcacycline B (a cyclic nonapeptide)	[74]
<i>Capsicum annuum L</i>	Silver	Protein	[75]
<i>Hibiscus</i>	Gold	rosa sinensis and proteins, vitamin C, organic acids (essentially malic acid), flavinoids and anthocyanins	[76]
<i>Cinnamomum zeylanicum</i>	Gold	terpenoids like: eugenol, cinnamaldehyde	[77]
<i>Murraya Koenigii</i>	silver and gold	Carbazole alkaloids, flavonoids and polyphenols	[78]
<i>banana peel</i>	Silver	pectin, cellulose, hemicelluloses and protein	[79]
<i>pongamia pinnata (L) pierre</i>	Silver	flavones	[80]
<i>Macroteloma uniflorum</i>	Silver	Polyphenol	[58]
<i>Artocarpus heterophyllus Lam</i>	Silver	Jacalin(lectin which is a single major protein)	[81]
<i>Trigonella foenum-graecum</i>	Gold	protein, vitamin C, niacin, potassium, and diosgenin	[82]
<i>Memecylon edule</i>	silver and gold	Saponin	[38]

Table 4. antibacterial activity of biosynthesized Ag NPs

<i>Staphylococcus aureus</i> (ATCC25923)		<i>Enterococcus faecalis</i> (ATCC51299)		<i>Escherichia coli</i> (ATCC 25922)		<i>Pseudomonas aeruginosa</i> (ATCC27853)	
MIC	MBC	MIC	MBC	MIC	MBC	MIC	MBC
EXTRACT	128	ND	>128	ND	>128	ND	>128
Ag NPs	16	ND	32	ND	4	ND	8

ND: Not determined (>128 µg/ml)

Table 5. shows some of the different plants used in the synthesis of nanoparticles and their different sizes and their antibacterial properties compared to the preparation of silver nanoparticles in this study.

Plant	Type of NPs	Size (nm)	antibacterial effect	References
olive	silver	20-25 nm	This study showed that these nanoparticles at a concentration of 0.03-0.07 mg / ml significantly increased bacterial growth against multidrug-resistant <i>Staphylococcus aureus</i> ( <i>S. aureus</i> ), <i>Pseudomonas aeruginosa</i> ( <i>P. aeruginosa</i> ) and <i>Escherichia coli</i> ( <i>E coli</i> ) restrained.	[86]
<i>Vitex Negundo L</i>	silver	10-30 nm	The nanoparticles showed antibacterial activity in both gram-positive and gram-negative bacteria	[87]
<i>Pedalium murex</i>	silver	10-150 nm	Antibacterial activity increased with increasing concentration of nanoparticles	[88]
<i>Sesbania grandiflora</i>	silver	10-25 nm	The synthesized AgNPs showed strong antibacterial activity against multidrug-resistant bacteria (MDRs) such as <i>Salmonella enterica</i> and <i>Staphylococcus aureus</i> .	[89]

In fact, these functional groups diminish the stability of silver ions and subsequently their production yields.

Antibacterial effect of biosynthesized Ag NPs survey on gram positive and gram negative bacteria. The MIC results of biosynthesized Ag NPs on *E. faecalis* and *S. aureus* obtained 8 and 4 µg/mL and *P. aeruginosa* and *E. coli* obtained 16 and 4 µg/mL (Table 4). Synthesized nanoparticles have a significant antibacterial effect compared to the extract. The MBC test of Ag NPs showed that there was no result observed for testing all bacteria.

The antibacterial effect of biosynthesized Ag NPs is related to cell wall structure in gram-negative and gram-positive bacteria [83]. The sulfur and phosphorus atoms present in cell wall of bacteria. The silver tends to interact these atoms, so silver can kill bacteria by reacting with the cell wall of bacteria. Gram positive bacteria contain rigid polysaccharide in its cell wall, which makes it difficult for silver to penetrate the walls of these bacteria[84]. Hence, inhibitory activity of Ag NPs is stronger in gram-negative than gram-positive bacteria [85].

## CONCLUSIONS

Silver nanoparticles were synthesized using *Euphorbia Pseudocactus Berger* (*Euphorbiaceae*) extract. existing Biomolecules in the plant extract act as fast bioreduction of silver ions during the formation nanoparticles. The average size of biosynthesized Ag NPs was determined 5.48-60 nm with an average diameter of about 9.16 -20.31 nm. Antibacterial results show good effect of biosynthesized nanoparticles on gram positive and gram negative bacteria. Moreover, the simulation results for XRD and UV-vis are in

good agreement with experimental measurements. So, biosynthesized nanoparticles can be utilized as an antibacterial agent in medical and industrial devices and tools.

## ACKNOWLEDGMENTS

The authors kindly thank to Shiraz University of Medical Sciences for financial support of the study [grant No. 97-01-74-17873].

## CONFLICT OF INTEREST

The authors declare there is no any conflict of interest.

## REFERENCES

1. Alghoraihi, I. and R. Zein, *Silver Nanoparticles: Advances in Research and Applications is Approaching*.
2. Zhang X-F, Liu Z-G, Shen W, Gurunathan S. Silver Nanoparticles: Synthesis, Characterization, Properties, Applications, and Therapeutic Approaches. International Journal of Molecular Sciences. 2016;17(9):1534.
3. Caro C, M P, Klippstein R, Pozo D, P A. Silver Nanoparticles: Sensing and Imaging Applications. *Silver Nanoparticles: InTech*; 2010.
4. Kouhbanani, M.A.J., et al., *Green Synthesis and Characterization of Spherical Structure Silver Nanoparticles Using Wheatgrass Extract*. Journal of Environmental Treatment Techniques, 2019. 7(1): p. 142-149.
5. Kouhbanani, M.A.J., et al., *Green Synthesis of Spherical Silver Nanoparticles Using *Ducrosia Anethifolia* Aqueous Extract and Its Antibacterial Activity*. Journal of Environmental Treatment Techniques, 2019. 7(3): p. 461-466.
6. Loiseau A, Asila V, Boitel-Aullen G, Lam M, Salmain M, Boujday S. Silver-Based Plasmonic Nanoparticles for and Their Use in Biosensing. Biosensors. 2019;9(2):78.
7. Mandal, A.K., *Silver nanoparticles as drug delivery vehicle against infections*. Glob J Nanomed, 2017. 3(2): p. 555607.
8. Pradeepa, V., T. Sriran, and M. Sujatha, *Studies on drug delivery efficacy of silver nanoparticles synthesized using human serum albumin as tamoxifen carriers in MCF-7 cell line*. Int J Sci Res, 2017. 6: p. 1881-1888.
9. Simbine EO, Rodrigues LdC, Lapa-Guimaraes J, Kamimura

- ES, Corassin CH, Oliveira CAFd. Application of silver nanoparticles in food packages: a review. *Food Science and Technology*. 2019;39(4):793-802.
10. Tripathi RM, Kumar N, Shrivastav A, Singh P, Shrivastav BR. Catalytic activity of biogenic silver nanoparticles synthesized by *Ficus panda* leaf extract. *Journal of Molecular Catalysis B: Enzymatic*. 2013;96:75-80.
  11. Verma, P. and S.K. Maheshwari, *Applications of Silver nanoparticles in diverse sectors*. International Journal of Nano Dimension, 2019. 10(1): p. 18-36.
  12. O.-T WJ. K. Nakanishi, Infrared absorption spectroscopy — practical. *Journal of Molecular Structure*. 1970;5(3):244.
  13. Pavia, D.L., et al., *Introduction to spectroscopy*. 2008: Cengage Learning.
  14. Bazmandeh, A.Z., et al., *Green Synthesis and Characterization of Biocompatible Silver Nanoparticles using Stachys lavandulifolia Vahl. Extract and Their Antimicrobial Performance Study*. *Journal of Environmental Treatment Techniques*, 2020. 8(1): p. 284-290.
  15. Rai M, Yadav A, Gade A. Silver nanoparticles as a new generation of antimicrobials. *Biotechnology Advances*. 2009;27(1):76-83.
  16. Ravishankar Rai, V., *Nanoparticles and their potential application as antimicrobials*. 2011.
  17. Flores-Rojas GG, López-Saucedo F, Bucio E. Gamma-irradiation applied in the synthesis of metallic and organic nanoparticles: A short review. *Radiation Physics and Chemistry*. 2020;169:107962.
  18. Li Y, Kim YN, Lee EJ, Cai WP, Cho SO. Synthesis of silver nanoparticles by electron irradiation of silver acetate. *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms*. 2006;251(2):425-8.
  19. Crivellaro S, Guadagnini A, Arboleda DM, Schinca D, Amendola V. A system for the synthesis of nanoparticles by laser ablation in liquid that is remotely controlled with PC or smartphone. *Review of Scientific Instruments*. 2019;90(3):033902.
  20. Adner D, Noll J, Schulze S, Hietschold M, Lang H. Aspherical silver nanoparticles by thermal decomposition of a single-source-precursor. *Inorganica Chimica Acta*. 2016;446:19-23.
  21. Ahlawat DS, Kumari R, Rachna, Yadav I. Synthesis and Characterization of Sol-Gel Prepared Silver Nanoparticles. *International Journal of Nanoscience*. 2014;13(01):1450004.
  22. Bae E-J, Park H-J, Park J-S, Yoon J-Y, Kim Y-H, Choi K-H, et al. Effect of Chemical Stabilizers in Silver Nanoparticle Suspensions on Nanotoxicity. *Bulletin of the Korean Chemical Society*. 2011;32(2):613-9.
  23. Kanmani P, Lim ST. Synthesis and structural characterization of silver nanoparticles using bacterial exopolysaccharide and its antimicrobial activity against food and multidrug resistant pathogens. *Process Biochemistry*. 2013;48(7):1099-106.
  24. Maksimović M, Omanović-Mikličanin E. Towards green nanotechnology: maximizing benefits and minimizing harm. *IFMBE Proceedings*: Springer Singapore; 2017. p. 164-70.
  25. Tamilselvan S, Ashokkumar T, Govindaraju K. Microscopy based studies on the interaction of bio-based silver nanoparticles with *Bombyx mori* Nuclear Polyhedrosis virus. *Journal of Virological Methods*. 2017;242:58-66.
  26. Wang C, Kim YJ, Singh P, Mathiyalagan R, Jin Y, Yang DC. Green synthesis of silver nanoparticles by *Bacillus methylotrophicus*, and their antimicrobial activity. *Artificial Cells, Nanomedicine, and Biotechnology*. 2015;1-6.
  27. Willner I, Basnar B, Willner B. Nanoparticle-enzyme hybrid systems for nanobiotechnology. *FEBS Journal*. 2006;274(2):302-9.
  28. R K, G G, A J, M G. Rapid Green Synthesis of Silver Nanoparticles (AgNPs) Using (*Prunus persica*) Plants extract: Exploring its Antimicrobial and Catalytic Activities. *Journal of Nanomedicine & Nanotechnology*. 2017;08(04).
  29. Ahmad S, Munir S, Zeb N, Ullah A, Khan B, Ali J, et al. Green nanotechnology: a review on green synthesis of silver nanoparticles — an ecofriendly approach . *International Journal of Nanomedicine*. 2019;Volume 14:5087-107.
  30. Beheshtkho N, Kouhbanani MAJ, Savardashtaki A, Amani AM, Taghizadeh S. Green synthesis of iron oxide nanoparticles by aqueous leaf extract of *Daphne mezereum* as a novel dye removing material. *Applied Physics A*. 2018;124(5).
  31. Jadidi Kouhbanani MA, Beheshtkho N, Amani AM, Taghizadeh S, Beigi V, Zakeri Bazmandeh A, et al. Green synthesis of iron oxide nanoparticles using *Artemisia vulgaris* leaf extract and their application as a heterogeneous Fenton-like catalyst for the degradation of methyl orange. *Materials Research Express*. 2018;5(11):115013.
  32. Kouhbanani MAJ, Beheshtkho N, Taghizadeh S, Amani AM, Alimardani V. One-step green synthesis and characterization of iron oxide nanoparticles using aqueous leaf extract of *Teucrium polium* and their catalytic application in dye degradation. *Advances in Natural Sciences: Nanoscience and Nanotechnology*. 2019;10(1):015007.
  33. Lohrasbi S, Kouhbanani MAJ, Beheshtkho N, Ghasemi Y, Amani AM, Taghizadeh S. Green Synthesis of Iron Nanoparticles Using *Plantago major* Leaf Extract and Their Application as a Catalyst for the Decolorization of Azo Dye. *BioNanoScience*. 2019;9(2):317-22.
  34. Nabikhan A, Kandasamy K, Raj A, Alikunhi NM. Synthesis of antimicrobial silver nanoparticles by callus and leaf extracts from saltmarsh plant, *Sesuvium portulacastrum* L. *Colloids and Surfaces B: Biointerfaces*. 2010;79(2):488-93.
  35. Raghuandan D, Bedre MD, Basavaraja S, Sawle B, Manjunath SY, Venkataraman A. Rapid biosynthesis of irregular shaped gold nanoparticles from macerated aqueous extracellular dried clove buds (*Syzygium aromaticum*) solution. *Colloids and Surfaces B: Biointerfaces*. 2010;79(1):235-40.
  36. Rajesh, S., et al., *Biosynthesis of silver nanoparticles using *Ulva fasciata* (Delile) ethyl acetate extract and its activity against *Xanthomonas campestris* pv. *malvacearum**. *Journal of Biopesticides*, 2012. 5: p. 119.
  37. Mittal AK, Chisti Y, Banerjee UC. Synthesis of metallic nanoparticles using plant extracts. *Biotechnology Advances*. 2013;31(2):346-56.
  38. Elavazhagan, T. and K.D. Arunachalam, *Memecylon edule* leaf extract mediated green synthesis of silver and gold nanoparticles. *International Journal of Nanomedicine*, 2011. 6: p. 1265.
  39. Newman DK, Kolter R. A role for excreted quinones in extracellular electron transfer. *Nature*. 2000;405(6782):94-7.
  40. Manandhar, N.P., *Plants and people of Nepal*. 2002: Timber press.
  41. Watanabe, T., et al., *A hand book of medicinal plants of*

- Nepal.* 2005.
42. Manoharan S, Kavitha K. Anticarcinogenic and antilipidperoxidative effects of *Tephrosia purpurea*(Linn.) Pers. in 7, 12-dimethylbenz(a)anthracene (DMBA) induced hamster buccal pouch carcinoma. Indian Journal of Pharmacology. 2006;38(3):185.
  43. Abdelrahman E, Abdel-Monem A. New abietane diterpenes from *Euphorbia pseudocactus berger* (Euphorbiaceae) and their antimicrobial activity. Pharmacognosy Magazine. 2016;12(46):346.
  44. Aghaei, M., et al., *Cytotoxic activities of Euphorbia kopotdaghi against OVCAR-3 and EJ-138 cell lines*. Journal of HerbMed Pharmacology, 2015. 4.
  45. Ashraf A, Sarfraz RA, Rashid MA, Shahid M. Antioxidant, antimicrobial, antitumor, and cytotoxic activities of an important medicinal plant (*Euphorbia royleana*) from Pakistan. Journal of Food and Drug Analysis. 2015;23(1):109-15.
  46. Aslanturk, O.S. and T.A. Celik, *Antioxidant, cytotoxic and apoptotic activities of extracts from medicinal plant Euphorbia platyphyllus L.* J Med Plants Res, 2013. 7(19): p. 1293-304.
  47. Sidambaran, R.R., M. Dinesh, and E. Jayalakshmi, *An in vitro study of cytotoxic activity of Euphorbia hirta on Hep2 cells of human epithelioma of larynx*. Int. J. Pharm. Pharm. Sci, 2011. 3(101): p. 3.
  48. Abubakar, E., *Antibacterial activity of crude extracts of Euphorbia hirta against some bacteria associated with enteric infections*. Journal of Medicinal Plants Research, 2009. 3(7): p. 498-505.
  49. Gayathri, A. and K.V. Ramesh, *Antifungal activity of Euphorbia hirta L. inflorescence extract against Aspergillus flavus-A mode of action study*. International Journal of Current Microbiology and Applied Sciences, 2013. 4: p. 31-37.
  50. Kader, J., et al., *Antibacterial activities and phytochemical screening of the acetone extract from Euphorbia hirta*. International Journal of Medicinal Plant Research, 2013. 2(4): p. 209-214.
  51. Rajeh MAB, Zuraini Z, Sasidharan S, Latha LY, Amutha S. Assessment of *Euphorbia hirta* L. Leaf, Flower, Stem and Root Extracts for Their Antibacterial and Antifungal Activity and Brine Shrimp Lethality. Molecules. 2010;15(9):6008-18.
  52. Rao, K.V.B., et al., *Antibacterial and antifungal activity of Euphorbia hirta l. Leaves: A comparative study*. Journal of Pharmacy Research, 2010. 3(3): p. 548.
  53. Garipelli, N., et al., *Anti-inflammatory and anti-oxidant activities of ethanolic extract of Euphorbia thymifolia Linn whole plant*. International Journal of Pharmacy & Pharmaceutical Sciences, 2012. 4: p. 516-519.
  54. Kusumoto N, Aburai N, Ashitani T, Takahashi K, Kimura K-i. Pharmacological Prospects of Oxygenated Abietane-Type Diterpenoids from *Taxodium distichum* Cones. Advances in Biological Chemistry. 2014;04(02):109-15.
  55. Sandhyarani, G. and K. Kumar, *Insecticidal activity of ethanolic extract of leaves of Euphorbia nivulia*. International J. of Pharmacological Screening Methods, 2014. 4(2): p. 102-104.
  56. Wu Q-C, Tang Y-P, Ding A-W, You F-Q, Zhang L, Duan J-A. <sup>13</sup>C-NMR Data of Three Important Diterpenes Isolated from *Euphorbia* Species. Molecules. 2009;14(11):4454-75.
  57. González MA. Aromatic abietane diterpenoids: their biological activity and synthesis. Natural Product Reports. 2015;32(5):684-704.
  58. Vidhu VK, Aromal SA, Philip D. Green synthesis of silver nanoparticles using *Macrotyloma uniflorum*. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy. 2011;83(1):392-7.
  59. Kannan RRR, Arumugam R, Ramya D, Manivannan K, Anantharaman P. Green synthesis of silver nanoparticles using marine macroalgae *Chaetomorpha linum*. Applied Nanoscience. 2012;3(3):229-33.
  60. Baghizadeh A, Ranjbar S, Gupta VK, Asif M, Pourseyedi S, Karimi MJ, et al. Green synthesis of silver nanoparticles using seed extract of *Calendula officinalis* in liquid phase. Journal of Molecular Liquids. 2015;207:159-63.
  61. Niraimathi KL, Sudha V, Lavanya R, Brindha P. Biosynthesis of silver nanoparticles using *Alternanthera sessilis* (Linn.) extract and their antimicrobial, antioxidant activities. Colloids and Surfaces B: Biointerfaces. 2013;102:288-91.
  62. Sinha SN, Paul D, Halder N, Sengupta D, Patra SK. Green synthesis of silver nanoparticles using fresh water green alga *Pithophora oedogonia* (Mont.) Wittrock and evaluation of their antibacterial activity. Applied Nanoscience. 2014;5(6):703-9.
  63. Umoren, S., I. Obot, and Z. Gasem, *Green synthesis and characterization of silver nanoparticles using red apple (Malus domestica) fruit extract at room temperature*. J Mater Environ Sci, 2014. 5(3): p. 907-914.
  64. Rostami-Vartooni A, Nasrollahzadeh M, Alizadeh M. Green synthesis of seashell supported silver nanoparticles using *Bunium persicum* seeds extract: Application of the particles for catalytic reduction of organic dyes. Journal of Colloid and Interface Science. 2016;470:268-75.
  65. Dubey SP, Lahtinen M, Särkkä H, Sillanpää M. Bioprospective of *Sorbus aucuparia* leaf extract in development of silver and gold nanocolloids. Colloids and Surfaces B: Biointerfaces. 2010;80(1):26-33.
  66. Miri, A., et al., *Green synthesis of silver nanoparticles using *Salvadora persica* L. and its antibacterial activity*. Cellular and Molecular Biology, 2016. 62(9): p. 46-50.
  67. Banerjee P, Satapathy M, Mukhopadhyay A, Das P. Leaf extract mediated green synthesis of silver nanoparticles from widely available Indian plants: synthesis, characterization, antimicrobial property and toxicity analysis. Bioresources and Bioprocessing. 2014;1(1).
  68. Vijay Kumar PPN, Pammi SVN, Kollu P, Satyanarayana KVV, Shameem U. Green synthesis and characterization of silver nanoparticles using *Boerhaavia diffusa* plant extract and their anti bacterial activity. Industrial Crops and Products. 2014;52:562-6.
  69. Ahmed S, Saifullah, Ahmad M, Swami BL, Ikram S. Green synthesis of silver nanoparticles using *Azadirachta indica* aqueous leaf extract. Journal of Radiation Research and Applied Sciences. 2016;9(1):1-7.
  70. Ghaffari-Moghaddam M, Hadi-Dabanlou R. Plant mediated green synthesis and antibacterial activity of silver nanoparticles using *Crataegus douglasii* fruit extract. Journal of Industrial and Engineering Chemistry. 2014;20(2):739-44.
  71. Sadeghi B, Gholamhosseinpoor F. A study on the stability and green synthesis of silver nanoparticles using *Ziziphora tenuior* (Zt) extract at room temperature. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy. 2015;134:310-5.

72. Siddiqui MR, Khan M, Khan, Adil, Tahir, Tremel W, et al. Green synthesis of silver nanoparticles mediated by *Pulicaria glutinosa* extract. *International Journal of Nanomedicine*. 2013;1507.
73. Ahmad N, Sharma S. Green Synthesis of Silver Nanoparticles Using Extracts of *Ananas comosus*. *Green and Sustainable Chemistry*. 2012;02(04):141-7.
74. Bar H, Bhui DK, Sahoo GP, Sarkar P, De SP, Misra A. Green synthesis of silver nanoparticles using latex of *Jatropha curcas*. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2009;339(1-3):134-9.
75. Li S, Shen Y, Xie A, Yu X, Qiu L, Zhang L, et al. Green synthesis of silver nanoparticles using *Capsicum annuum* L. extract. *Green Chemistry*. 2007;9(8):852.
76. Philip D. Green synthesis of gold and silver nanoparticles using *Hibiscus rosa sinensis*. *Physica E: Low-dimensional Systems and Nanostructures*. 2010;42(5):1417-24.
77. Smitha SL, Philip D, Gopchandran KG. Green synthesis of gold nanoparticles using *Cinnamomum zeylanicum* leaf broth. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*. 2009;74(3):735-9.
78. Philip D, Unni C, Aromal SA, Vidhu VK. *Murraya Koenigii* leaf-assisted rapid green synthesis of silver and gold nanoparticles. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*. 2011;78(2):899-904.
79. Ibrahim HMM. Green synthesis and characterization of silver nanoparticles using banana peel extract and their antimicrobial activity against representative microorganisms. *Journal of Radiation Research and Applied Sciences*. 2015;8(3):265-75.
80. Raut RW, Kolekar NS, Lakkakula JR, Mendulkar VD, Kashid SB. Extracellular synthesis of silver nanoparticles using dried leaves of *pongamia pinnata* (L) pierre. *Nano-Micro Letters*. 2010;2(2):106-13.
81. Jagtap UB, Bapat VA. Green synthesis of silver nanoparticles using *Artocarpus heterophyllus* Lam. seed extract and its antibacterial activity. *Industrial Crops and Products*. 2013;46:132-7.
82. Aswathy Aromal S, Philip D. Green synthesis of gold nanoparticles using *Trigonella foenum-graecum* and its size-dependent catalytic activity. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*. 2012;97:1-5.
83. Sun, Q, et al., *Green synthesis of silver nanoparticles using tea leaf extract and evaluation of their stability and antibacterial activity*. *Colloids and surfaces A: Physicochemical and Engineering aspects*, 2014. **444**: p. 226-231.
84. Hamouda T, Baker JR. Antimicrobial mechanism of action of surfactant lipid preparations in enteric Gram-negative bacilli. *Journal of Applied Microbiology*. 2000;89(3):397-403.
85. Tamboli DP, Lee DS. Mechanistic antimicrobial approach of extracellularly synthesized silver nanoparticles against gram positive and gram negative bacteria. *Journal of Hazardous Materials*. 2013;260:878-84.
86. Khalil MMH, Ismail EH, El-Baghdady KZ, Mohamed D. Green synthesis of silver nanoparticles using olive leaf extract and its antibacterial activity. *Arabian Journal of Chemistry*. 2014;7(6):1131-9.
87. Zargar M, Hamid AA, Bakar FA, Shamsudin MN, Shameli K, Jahanshiri F, et al. Green Synthesis and Antibacterial Effect of Silver Nanoparticles Using *Vitex Negundo* L. *Molecules*. 2011;16(8):6667-76.
88. Anandalakshmi K, Venugopal J, Ramasamy V. Characterization of silver nanoparticles by green synthesis method using *Pedalium murex* leaf extract and their antibacterial activity. *Applied Nanoscience*. 2015;6(3):399-408.
89. Das J, Paul Das M, Velusamy P. *Sesbania grandiflora* leaf extract mediated green synthesis of antibacterial silver nanoparticles against selected human pathogens. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*. 2013;104:265-70.