

REVIEW ARTICLE

Tungsten Disulfide Nanomaterials (WS₂ NM) Application in Biosensors and Nanomedicine: A review

Sedigheh Niknam ¹, S. Ahmad Dehdast ², Omid Pourdakan ³, Mohammad Shanbani ²,
Mohammad Kazem Koohi ^{4*}

¹ Institute of Nanoscience and Nanotechnology, University of Kashan, Kashan, Iran

² Department of Biochemistry, School of Medicine, Iran University of Medical Sciences, Tehran, Iran

³ Faculty of Advance Technologies in Medicine, Iran University of Medical Sciences, Tehran, Iran

⁴ Department of Comparative Biosciences, Faculty of Veterinary Medicine, University of Tehran, Tehran, Iran

ARTICLE INFO

Article History:

Received 25 May 2022

Accepted 25 Jul 2022

Published 01 Aug 2022

Keywords:

Tungsten disulfide
(WS₂) Nanomaterial
Biosensor
Bio-imaging
Photothermal/
Radiotherapy
Biocompatibility

ABSTRACT

The development of nanotechnology has proposed new routes in the design of the novel device for medical and biological applications. Tungsten disulfide (WS₂) is a transition metal dichalcogenides. Tungsten disulfide nanomaterial (WS₂ NM) are new nanostructures that can be used as a new option in bio-nanomedicine. Recently, Tungsten disulfide nanomaterial such as WS₂ nanotubes, nanoparticles, quantum dots, and WS₂ based nanocomposites have been used in some medical and biological science research. WS₂ nanomaterial present chemical, physical, optical and electronic properties that can be exploited in a range of various applications. In this article, we discuss and report chemophysical relevant properties of tungsten disulfide nanostructures and the main achievements reached by using of this nanomaterial and related composite in biomedical research and biosensors, especially those involving electrochemical biosensors, optical biosensors, biomedical imaging, Photothermal therapy, radiotherapy, tissue engineering, and biocompatible anticancer and antibacterial agent.

How to cite this article

Niknam S., Ahmad Dehdast S., Pourdakan O., Shanbani M., Kazem Koohi M. Tungsten Disulfide Nanomaterials (WS₂ NM) Application in Biosensors and Nanomedicine, A review. *Nanomed Res J*, 2022; 7(3): 214-226. DOI: 10.22034/nmrj.2022.03.001

INTRODUCTION

In the last few decades, nanomaterials have been extensively used in a number of multidisciplinary science that include material science, environmental science, food industry, cosmetic, and medical sciences [1, 2]. The advantage of nanotechnology has increased our competence to develop the material's physicochemical properties to enable their use in biomedical applications such as diagnosis, drug delivery, nano-implants, bacterial treatment and cancer therapy. Various metal nanoparticles have been widely exploited for a wide range aforementioned goals [3, 4]. Recently, the synthesis and application of tungsten

disulfide nanomaterials (WS₂ NM) and related nanostructures in biomedical science increased, especially for diagnostic and treatment purposes [5, 6]. Tungsten disulfide (WS₂) is a member of group 6 transition metal dichalcogenides (G6-TMDs), including MoS₂, MoSe₂, MoTe₂, WS₂ and WSe₂, which consist of two parts, first part is transition-metals (Mo, W, Nb, etc.) and second part is chalcogen elements (S, Se, Te) [7-9]. Tungsten (W) is the heaviest transition metal in the transition metal dichalcogenides (TMDs) common family, also in comparison with the Mo, W is less toxic and inexpensive, for this reason tungsten have a high potential for a broad range of application in research and industry [10]. Tungsten

* Corresponding Author Email: mkkoochi@ut.ac.ir

Table 1. Electrochemical and optical biosensors base on tungsten disulfide nanomaterials

Biosensor	Biorecognition	Nanomaterial	Detection	Reference
Electrochemical	DNA	AuNPs/WS2-Gr nanostructure	impedimetric	[32]
	ferritin antibodies	tungsten disulfide -quantum dots	voltometric	[35]
	c-Met protein	(WS2 QDs)-AU	voltammetry	[34]
	Cell-based	(WS2/MWCNTs-OH)	impedimetric	[26]
	sulfamethazine(SMZ)	carbon quantum dots-tungsten disulfide nanocomposite glassy carbon electrode (CQDs-WS2/GCE)	voltometric	[36]
Optical	Cefixime residues in milk	tungsten disulfide quantum dots (WS2 QDs)	ratiometric fluorescent sensor	[33]
	Dopamine	WS2 QDs	fluorescent	[37]
	Nitrofurazone	Tungsten disulfide (WS2) Dot	fluorescent probes	[30]
	DNA	graphene coated surface plasmon resonance (SPR) sensor with Tungsten Disulfide (WS2)	SPR	[38]

disulfide as a transition metal dichalcogenides have superb electronic, thermal, magnetic, and optical properties due to its special structure [11-14]. Until now, several WS2 based nanomaterial with various structures (nanotubes, quantum dots [5], nanoparticles [15], nanotube [16], nanosheets [17], hybrid nanomaterial and nanocomposites [18, 19], etc.) were synthesized base on the special chemophysical structure of tungsten. The other hand, WS2 NM are widely interest for scientist among the medical research owing to their excellent optical activity, good conductivity, biocompatibility, less toxicity, which results from their high chemical and physical stability, as well as easy functionalization with organic and inorganic chemical and biologically active molecules or atoms [11, 13, 20-23]. Although WS2 NM has increasing been used in the medical research, there is no comprehensive review of their applications in nanomedicine. Therefore, in this review, we have summarized the available approaches of medical research applications of WS2 NM, as well as the used techniques in researches to evaluation of biological and medical effect of WS2 NM and discuss about achieved results.

BIOSENSORS

Biosensing systems

Biosensors developed as a combination of bio-receptors and transducers that are classified in accordance to their elements. These products are commonly divided into three categories based on transducers, including electrochemical, optical, and conductivity methods. Meanwhile, the classification of biomarkers is based on molecules, cells, and tissues (Fig. 1). Typically, the fabrication of a biosensor requires three steps as the following. The first step involves the reaction of the biomarker with the desired analyte, while the integration of a transducer occurs through the second step and the last step implicates the fixation/movement of a biological component to the transducer. It is considerable that the quality of these three stages and the currency of the components are incredibly effective in achieving successful results [24, 25].

The massive interest invested in biosensors is due to their speed and accuracy in the detection of small analytes. In line with this fact, the rate of combined biosensors with diverse nanomaterials and biomaterials for biomedical research has been extended. Recently, the products of nanobiosensor

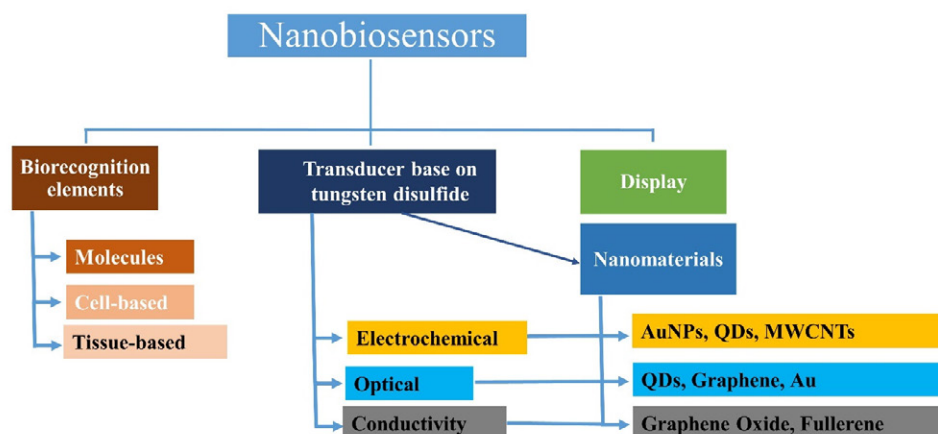


Fig.1. Nanobiosensor classification base on tungsten disulfide

presented a new route for the detection of biomolecular interactions [26]. An extensive amount of research was conducted on loading techniques and support carriers for designing and manufacturing electrochemical biosensors [27]. The quick development of nanomaterials into a significant research area was caused by their particular chemical and physical properties for producing biosensors with improved analytical performance [28].

Transducers are one of the vital components in biosensors that are responsible for exhibiting the responses of biomarker interactions with the target analyte through a recognizable and repeatable manner that requires the conversion of an specific biochemical reaction energy into visual structures. The high surface-to-volume ratio of nanomaterials is reasonable since transducers are accountable for the promoting a more accurate identification of biochemical reactions [26, 29]. Moreover, the electromechanical properties of nanoparticles can be an excellent aid for the biosensor technology.

The highly anisotropic bonding of WS₂, which affects the electrical and mechanical properties, provided extremely interesting results in catalytic reactions [30]. Nowadays, researchers are focused on enhancing the sensitivity and specificity of biosensors by concentrating on the quality of nanobiosensor evolution and fabrication via surface modification, which implicate the application of different nanomaterials such as nanosheets [26, 31], nanoparticles [32] or quantum dot [33] in order to extend the affinity and improve signal

amplification (Table1). The following sections present a summary of recent advances of using WS₂ as a sensing platform for biomolecule detection by leveraging its optical and electrochemical properties, while particularly highlighting its applications throughout the sensing field.

WS₂-based electrochemical biosensor

For a very long time, electrochemical biosensors, such as semiconductors and screen-printed electrodes, were used for various applications in numerous fields. In electrochemical based biosensors, the amplification of electrochemical signals by NPS leads to the development of several nano-hybrid compounds that are capable of contributing to the formation of strong biosensors as a quick, simple, and sensitive method for biomolecule identification. Electroactive metal tungsten (W) is extensively exerted in electrochemical biosensors. The electrical conductivity of WS₂ can be improved by being combined with conductive compounds, similar to metallic nanoparticles such as gold, silver, and platinum, through the utilization of one-step or sequential electrodeposition techniques [34]. The superior sensing performance of proposed WS₂-based sensor can be successfully employed for the observance of DNA hybridization, enzymes, and proteins, as well as environmental contamination and medical diagnostics [26].

In line with these facts, Ke-Jing Huang et al. presented a straightforward method for creating a robust and conductive interface for DNA hybridization based on electrochemical

detection [32]. This study demonstrated a dual signal amplification platform that is built on the combination of tungsten sulfide-graphene (WS₂-Gr) composite and Au nanoparticles (AuNPs). The obtained conductivity can be satisfyingly maintained by ssDNA-AuNPs/WS₂-Gr, since the structures and characteristics of WS₂-Gr and AuNPs cannot be altered by the DNA-mediated noncovalent assembly of this nanostructure. This dual signal amplification method can distinguish the single/ three-base mismatched DNA sequences with remarkable selectivity, which can facilitate the detection of target DNA down to femtomolar scale. Their linear range of detectable DNA concentration was fourfold more superior than the other methods.

In another study, a biosurfactant was used for biomolecule functionalization and providing the stability of tungsten disulfide quantum dots. [35]. Next to requiring a lower rate of toxic chemicals applications, their process exerted functionalized QDs for the purpose of ferritin antibodies immobilization. The results of this study indicated the achievement of a proper selectivity, stability, and dynamic linear range out of their immunosensor. These QDs functionalized electrodes proved to be quite applicable for the creation of portable or point-of-care devices. This platform can facilitate the observance of an extensive range of additional diagnostic indicators, which are medically important, by simply switching the target bio-receptor. However, the main obstacle to this approach is the availability of biosurfactants for synthesizing quantum dots. Therefore, it is necessary to scale up the manufacturing of biosurfactants.

The combination of QDs with nanoparticles results in a type of semiconductor that is used as an electrochemical modifier to improve the sensitivity of biosensors toward the detection of proteins. Ramin Pourakbari et al. developed a new biosensing technique for performing the quick and precise detection of c-Met protein by the exertion of tungsten disulfide quantum dots (WS₂ QDs)-AU [34]. Their study implicated the modified electrochemical deposition of AuNPs, functionalized with WS₂ QDs, on GCE (glassy carbon electrode). Thereafter, the immobilization of c-Met bacteriophage was carried out on the modified electrode to be applied for the detection of c-Met protein (colon cancer biomarker) via an electrochemical biosensor.

The characteristics of newly developed cell-

based electrochemical sensors, such as the lack of labeling requirements, high sensitivity, simplicity, quickness, non-toxicity, and reusability, led to their robust application throughout in vitro toxicity assessments. Guanlan Wu et al. reported the usage of a simple method to create a hybrid material composed of WS₂ nanosheets and hydroxylated MWCNTs (WS₂/MWCNTs-OH) [26]. The substrate was a screen-printed carbon electrode (SPCE) with the advantages of requiring minimal costs, as well as being disposable and energy efficient. Modification with a WS₂/MWCNTs-OH composite resulted in increasing the rate of sensitive and selective behaviors. The Grass Carp Kidney (CIK) cell line was exerted as an effective toxicology model for identifying and tracking the alterations of electrochemical responses throughout the assessment of cell viability. In this study, the application of cyclic voltammetry and high-performance liquid chromatography (HPLC) was considered to examine the electrochemical reaction mechanism of CIK cells. The cytotoxic effects of 2,4,6-trichlorophenol (2,4,6-TCP), polystyrene nanoplastics (PSNPs) and bisphenol AF (BPAF) were detected by the electrochemical sensor to be compared with the proposed sensor through the course of MTT assay. This sensor is practically applied for determining the cytotoxicity of genuine chemical wastewater samples.

Furthermore, Yan Wang et al. suggested the application of WS₂-QD for the detection of sulfamethazine (SMZ) sensitivity through a label-free electrochemical aptasensing approach [36]. According to their experimental results, the idea of exerting electrochemical sensors can offer a straightforward, dependable, and efficient method for biosensing the trace of SMZ residue in environmental contamination monitoring and food safety detection. They also tried the application of WS₂-QD for detecting sulfamethazine (SMZ) sensitivity via a label-free electrochemical aptasensing approach and achieved similar results to their previous work.

WS₂-based optical biosensor

Upon the combination of an analyte and recognition components that lead to the formation of complexes, optical biosensors can provide the measurement of their surface's changes by the usage of optical instruments. Opcode-based fiber, evanescent wave fiber, resonant mirror, time-resolved fluorescence, interferometric, and surface

plasmon resonance biosensors are among the different types of optical biosensors.

These biosensors can be categorized into two classifications of the direct and indirect optical biosensor. Direct optical biosensors require a complex on the transducer surface for signal generation, while indirect optical biosensors implicate fluorophores or chromophores as their labels to identify binding events and amplify the signal. Although higher signal levels can be produced through indirect biosensing techniques, however, they are limited by non-specific binding and a high reagent cost for the labeling process. Considering how tungsten disulfide (WS2) QDs can stand as applicable candidates due to their essential optical and electrical features, WS2 QDs exhibited excellent fluorescent properties [33].

WS2-QD was applied in colon cancer evaluation for the detection of c-Met protein in serum samples [34] as an efficient probe for dopamine fluorescence detection of dopamine (DA) [37]. Also, Mahsa Haddad Irani-nezhad et al. [33] introduced the usage of a ratiometric fluorescence sensor for the measurement of Cefixime based on tungsten disulfide quantum dots (WS2 QDs) and fluorescein (CEF). In this study, bulk WS2 was subjected to the combined sonication solvothermal procedure at a low temperature to create WS2 QDs. The suggested ratiometric probe was able to configure the volume of CEF in various milk samples.

Moreover, Xinrong Guo et al. designed an optical biosensor that implicate a straightforward hydrothermal procedure for the production of luminescence from tungsten dots, which functions through sodium tungstate and reduced L-glutathione. Their biosensor involves the application of WS2 dots in the form of a fluorescent probe for the detection of nitrofurazone (NFZ) in nasal drops and water samples [30].

Recently, the attention of fundamental optical realizing electronics was attracted by Surface plasmon reverberation (SPR)-located biosensors on account of their hopeful applications in various fields such as healing diseases, biomolecules detection, biochemical discovery, and surroundings listening.

Parallel to this line of thought, it is noteworthy that graphene tiers can increase the sensitivity while decreasing the different conduct limits [38]. In this study, WS2 was inserted among the metal and graphene layers to increase the efficiency limits. An analysis was also performed on the

thickness impact of gold on the experimental structure. Although the disparity of SPR angle for unsuited DNA strands is relatively insignificant, yet this phenomenon is notably countable for complementary DNA strands. Therefore, it can be stated that the suggested biosensor can provide a novel route toward the detection of biomolecular interactions.

Considering the ability of WS2 to specify a 2D covalent network, it is a suitable substrate for immobilizing biospecies. Pingyao Wang et al. reported the development of a fluorescent probe by using 2D WS2 nanosheets and aptamer-modified core-shell upconversion nanoparticles as the acceptor and donor, respectively[31]. This novel, sensitive, and selective biosensor can be applied for the rapid and specified quantification of *E. coli*. Furthermore, WS2 nanosheets can function as excellent energy acceptors due to containing a broad absorption spectrum that can increase the efficiency. Therefore, this fluorescent biosensor can be a platform for the observance of different bacterial pathogens through the alteration of related specific aptamer.

The conductivity of WS2 NM

Conductivity and development of basic structure conductivity for the design of biosensors is important. WS2 NM are shown excellent conductivity for use in electronic and biosensor device. Hexagonal crystals are the basic structural units of two-dimensional tungsten disulfide nanomaterials, in which two sulfur atoms are bounded with a tungsten atom that form the S-W-S sandwiched layer. The combination of S-W-S layers is caused by the weak van der Waals forces. Also, dormant is the substance of transition-metal sulfide phase. In contrast, the characteristics of WS2 nanosheets can be drastically altered by reducing their sizes down to the range of nanoscale, while their active sites are positioned at their edges. Hence, the shifting of the electron band gap occurs from 1.4 eV to 2.0 eV throughout the bulk phase of nanosheets. WS2 nanosheets succeeded in garnering the investment of many in various domains due to their vast specific surface area, fascinating electrical conductivity, and unique electronic structures. Therefore, it is crucial to find the ability to manage the size, morphology, and crystal structure of WS2 nanosheets [39].

Deqing Zhang et al. reported the usage of sodium diethyldithiocarbamate (as the reducing

agent and sulfur source), tungsten hexachloride (as the tungsten source), and cetyltrimethylammonium bromide (as the surfactant) for synthesizing flat sheet-like tungsten disulfide that would contain a single crystal construction [17]. According to results, their facile, one-step hydrothermal route was successful in synthesizing the tungsten disulfide nanosheets. WS₂ nanosheets contain a single-crystal construction with a distinctive lamellar and porous shape along with significantly high specific surface area and electronic criteria. A practical method for the enhancement of electromagnetic shielding efficacy is the addition of conductive nanotubes to an insulating polymer matrix. The work of Jan Macutkevicius et al. claimed that due to the high aspect ratio of nanotubes, their addition to an insulating polymer matrix can effectively increase the electromagnetic shielding performance [40]. Apparently, WS₂ nanotubes and polymer matrixes contain relatively ohmic electrical connections.

Over the last few decades, a massive effort was paid into the production of innovative nanostructured hosts in order to improve cathode electronic conductivity and decrease the loss of soluble polysulfide intermediates. Notably, several carbon materials, with outstanding electronic conductivity, high specific surface area, and controlled construction, were able to successfully function as a sulfur host or conductive framework. Non-polar carbon-based compounds can improve the application of sulfur by facilitating the transportation of ions and electrons. Considering its mono-atomic sheet of carbon atoms, graphene is a popular (2D) substance among various carbonaceous materials. Weishan Li et al. reported the development of a coral-like reduced graphene oxide/tungsten sulfide hybrid in the form of a host for sulfur cathode at the University of Bristol [41]. This hybrid can prepare a 3D network for electronic conductivity and a large surface area for the chemical entrapment of intermediates. Their work presented the design of porous, 3D coral-like rGO/WS₂ composite by using a facile hydrothermal process to be exerted in the form of a cathode host for LSB. The notable potential of this composite for the discovery of high energy density and energy storage devices is undeniable.

On the other hand, the optical activities and electrical properties of atomically thin 2D metal dichalcogenide (TMDCs) materials, such as WS₂ and their composites with graphene or graphene oxide, attracted the attention of researchers in

recent years. Jaesool Shim et al. reported the successful preparation of a core-shell reduced graphene oxide (rGO) on tungsten sulfide (WS₂) nanostructure that was capable of catalyzing the four-electron oxidation-reduction reaction (ORR) in a 1 M KOH aqueous solution [42]. According to their results, nano-electrochemists provided the enhancement of a straightforward and super-efficient electrocatalyst by the exertion of an uncomplicated microwave irradiation procedure. They performed an assessment on the activity and stability of produced catalyst throughout methanol oxidation reaction and ORR in alkaline media.

Yuhua Xue et al. disclosed a one-step hydrothermal process for creating a novel core-sheath fiber with a graphene core and radially aligned tungsten disulfide sheath. An all-solid fiber-shaped supercapacitor was created by using two of these fibers as electrodes. They reported the ability of the sheath nanosheet array in generating numerous active sites and facilitating the occurrence of quick ion diffusion, while the high conductivity of fibers can be ascertained by the graphene core. The existence of extended capacitance, long-term stability, and exceptional flexibility in an electrode material can result in a unique contender for creating high-performance energy storage fibers [19].

A new allotropic form of carbon with stable 60-atom molecules was discovered in 1985 and labeled as "fullerene". The development of inorganic fullerene-like nanoparticles was driven by the intense interest in the distinct physical and chemical features of fullerene-like nanoparticles (IF-NP). These potentially unstable structures can bend and close in on themselves under specific circumstances, leading to the attachment of rim atoms and resembling graphite, while generating particles in the size range of 20 to 200 nm. The identification of this molecule sparked an active investigation into other potential carbon configurations. Considering their unique structures, MoS₂ and WS₂ nanoparticles proved to be excellent solid lubricants capable of improving friction and wearing throughout wet and dry environments with varying loads. In the report of Alberto De Stefani et al., orthodontic stainless steel wires were coated with the lubricant-containing nanoparticles of molybdenum and tungsten disulfide (MoS₂ and WS₂) to check the chances of causing improvements in the tribological qualities during the sliding of wires over the brackets [43].

They reported the relative reasonable cost and effectiveness of this approach in comparison to disulfides based on their characteristics and behavior.

BIOIMAGING AND RADIOTHERAPY

The WS₂-QD (3 nm and 28 nm) synthesized as enhancer for X-ray computed tomography (CT)/photoacoustic imaging (PA) due to its high atomic number and NIR absorption. Smaller particles temperature increase had higher temperature raise with NIR irradiation, therefore are better candidate for PTT. In vitro toxicity of WS₂-QD on HeLa and HepG 2 cells in different concentration showed cell viability higher than 85% for both cell lines. In vivo toxicity evaluation on mouse didn't show any sign of deviation in body weight, eating, drinking and normal activity. Biodistribution assessment showed accumulation in kidney, liver and spleen with no significant hepatic and renal dysfunction and after 30 days. Comparison between NIR alone, X-ray alone to NIR+WS₂ and RT+WS₂ treatment on 4T1 cell showed cell viability reduction to 97% and 75% in NIR alone and X-ray alone respectively and reduction to 39% and 31% in NIR+WS₂ and RT+WS₂ respectively. Synergic effect of using RT/PTT reduced cell viability to 6%. Effectiveness of a radio-sensitizer to tumor proliferation reduction measured by the sensitizer enhancement ratio (SER). For WS₂-QDs SER reported 1.22 and increased to 1.31 in combination with NIR. WS₂ QDs + NIR+ RT showed complete elimination of tumor in 5 days after treatment. WS₂ QDs were intravenously injected into the tail vein of BEL-7402 tumor-bearing BALB/c nude mice to investigate the photoacoustic (PA) signal of tumor at different time. After injection PA signal reach twice compared to before injection and lasted for 24 h. To investigate CT contrast performance in vitro, WS₂-QD compared to iopromide. WS₂-QD showed two times higher performance at the same concentration. To investigate CT contrast in vivo increased from 153 ± 4.2 to 332.7 ± 27.4 after WS₂-QD were injection to BEL-7402 tumor-bearing BALB/c mice. Results indicate that WS₂-QD is an excellent contrasting agent for CT and PA dual-modal imaging and synergistic therapy [5]. Nanomaterials have shown excellent potential in bioimaging. Design of new nanomaterial for Non-invasive monitoring is an attractive field in nanomedicine. Li et al. designed MPDA-WS₂@MnO₂ to use in CT/MSOT (multispectral

optoacoustic tomography)/MR imaging modalities. Polydopamine (PDA) - WS₂@manganese dioxide (MnO₂) nanocomposites has good biocompatibility and photothermal stability. Manganese dioxide (MnO₂)-based nanostructure produce Mn²⁺ ions which result in pH/H₂O₂-responsive activated T1-weighted MR signal. To investigate in vitro efficacy of MPDA-WS₂@MnO₂, by the 808 nm NIR laser at 1.5 W/cm² irradiate on it. Cytotoxicity of MPDA-WS₂@MnO₂ on 4T1 cells under 808 nm laser irradiation were done and at the highest concentration most cells were killed however no significant cytotoxicity was observed without laser irradiation even at highest concentration. MPDA-WS₂@MnO₂ structure showed SER up to 1.562 which had an increase compared to MPDA-WS₂ nanoparticles and confirm enhancement in sensitivity of tumor cells to X-ray due to O₂ generation. To investigate photoacoustic signaling at 808 nm different concentration of MPDA-WS₂@MnO₂ in different time interval and reached maximum level at 12 post-injection and showed 2.55-fold enhancement. Finally results shown that excellent achievement for imaging and thermoradiotherapy of hypoxic cancer [44].

PHOTOTHERMAL/ RADIATION THERAPY

Radiation Therapy is one of the methods to combat cancer and photothermal therapy (PTT) is a subset of radiation therapy in which use photosensitizer material to convert light to heat and ablate cancer cells. In this method a specific range of wavelength which is called Near-Infrared (NIR) radiate on PTT agents. In 2019 Lellouche et al. used tungsten disulfide (WS₂) nanocomposite as a PTT agent. WS₂ nanocomposites were functionalized by ceric ammonium nitrate-maghemite (CAN-mag) nanoparticles for three reasons: (1) enhance magnetization properties of WS₂-NT, (2) ability for second functionalization with polymers such as polyethyleneimine (PEI), Polyacrylic acid (PAA) and other molecules to increase therapeutic activities, (3) to reduce aggregation of WS₂-NT. WS₂-NT had diamagnetic properties on the other hand CAN-mg due to presence of iron-oxide nanoparticle had superparamagnetic activity. Photothermal therapy of WS₂-NT and WS₂-NT-CM were testing on Hela (cervical cancer) and MCF7 (breast cancer) cell lines by a 700 nm NIR laser. WS₂-NT treated Hela cells showed, 65% and 20% of cells dead, and detached respectively and in WS₂-NT treated MCF7 cells 50% were dead

and 50% were detached. On the other hand, WS₂-NT-CM treated Hela cells showed 95 % dead and 5% detachment and WS₂-NT treated MCF7 cells showed 85 % dead and 15% detachment. The reason of this difference is that WS₂-NT-CM accumulate in and near cells while WS₂-NT aggregate walls of blood vessels and cannot reach the tumor [6].

Jiang-Tao Wang et al. used one-step 'bottom-up' hydrothermal reaction to synthesize tungsten disulfide with PEGylated coat (WS₂-PEG) nanoparticles for CT-guided PTT in Murine breast cancer cells (4T1 cell line) and balb/c mice that bear 4T1 cell line which were subcutaneously injected. Photothermal stability was compared to indocyanine green (ICG) by the 808 nm laser (2 W/Cm²) 5 min irradiation with several cycles and showed good stability while ICG disintegrated. 4T1 cells with WS₂-PEG and irradiated by the 808 nm laser (2 W/Cm², 5 min) showed a cell viability drop to 5%. CT imaging and PTT in vivo investigation showed a stability in temperature at 52 for that local temperature in 4T1 cell bear mice treated with WS₂-PEG NPs and laser led to no sign of increase in tumor volume after 3 days also due to x-ray attenuation of tungsten atoms it can play contrast agent role for CT-imaging tumors. Comparisons between control group and group that received WS₂-PEG NPs in spleen, kidney, liver, lung and heart showed no difference and there was no significant weight-loss in NPS received mice. Result showed in biocompatibility low cytotoxicity of WS₂-PEG NPs [45].

WS₂ NM BASED Nanocarriers

Traditional drug delivery systems like oral and injection needed higher concentration of drugs to see therapeutic effect and administration this amount of drugs led to side effect in some patients. Recently controllable stimuli-responsive drug delivery systems which use of magnetic field, enzyme, ultrasound, light, pH or electrical stimulations developed. Hsiao et al. design an electric responsive delivery system using WS₂ due to their suitable electrical properties. WS₂ synthesis and functionalized by ligands which were thiol-terminated like thioglycolic acid (TGA), dimercaptosuccinic acid (MSA), and 2-ethanethiol (2ET) then non-covalently coated with polypyrrole (PPy) which is electrically conductive and for drug model 5-fluorouracil (5-FU) were choose. TGA-WS₂-PPy exhibit higher drug release (90%) compared to MSA and 2TE due to swelling effect.

Cytotoxicity of TGA-WS₂-PPy-FU on HaCaT cells in the absence of electrical stimulation showed no significant toxicity; however, under electrical stimulation, HaCaT cells died. To investigate in vivo drug release two patch were place on control group and other with drug and Raman mapping was performed to assess carrier penetration to skin. Results showed deeper penetration to skin under electrical stimuli in delivery system make this novel carrier appropriate candidate for externally-controlled model [46].

Sobhani et al. used design a dendrimers grafted Poly (N-Vinylcaprolactam) modified WS₂ nanosheets as a thermosensitive nanocarrier for Pioglitazone delivery. The synthesized structure were evaluated in simulated human blood fluid for in vitro treatment of diabetes. 18% and 98% of total drug were released in vitro within the 6 h at 37 C and at 50 C without IR irradiation, respectively. However drug released reached up to 100% of in presence near-infrared laser irradiation from modified WS₂ nanocarrier within 15 minutes [47].

WS₂ NM IN TISSUE ENGINEERING AND IMPLANT

Nanomaterial can be used to tissue engineering for fabrication of high performance scaffold, implant and medical device. The WS₂ nanomaterial are novel candidate for the development of tissue engineering and nanomedicine. Due to electrical and mechanical properties of tungsten disulfide (WS₂) they can be used in scaffold reinforcement, design in tissue engineering and drug delivery [5].

In orthodontic treatment tooth movement along archwire generates friction force between wire and bracket in opposite direction of orthodontic force. In the past the focus was on engineering bracket nowadays Lowering friction force is the main focus and can result in lower treatment time and risk of root resorption. For this purpose hexagonal structure (H) of molybdenum and tungsten disulfides (MoS₂ and WS₂) are suitable candidate due to excellent solid lubricant properties also in certain condition they can bend on themselves and create graphite-like structures. Burono et al. studied on coating effect of stainless steel (SS) with three groups of Ni, Ni+MoS₂ and Ni+WS₂ with Damon Q and In-Ovation self-ligating bracket and two different angles (0 and 5) for wire-bracket in dry and wet conditions. Nanoparticles were coated on the steels with electrodeposition method due to being controllable and to simulate wet condition,

artificial saliva was used. Coating thickness was reported 10 μ m, 20 μ m and 15 μ m for Ni, Ni+MoS₂ and Ni+WS₂ respectively. Not seen any sign of breakage at minimum binding but only Ni coated wire remains without damage at maximum binding in groups. Coating steels with nanoparticles showed more decrease in friction value compared to Ni-coated steel but there were no significant difference between Ni+WS₂ and Ni+MoS₂, latter showed lower decrease. In conclusion Ni+WS₂ and Ni+MoS₂ showed better features compared to neat stainless steel or Ni-coated Steel and significant reduce in friction between archwire and In-Ovation bracket (not Daman Q) in dry condition [48]. Orthodontic stainless steel wires developed by using fullerene-like WS₂. Redlich coated stainless steel (SS) with nickel-phosphorus and inorganic fullerene-like tungsten disulfide (WS₂) with electroless deposition. Friction coefficient exhibit notably decrease from 0.25 to 0.08 and friction forces decreased by up to 54%. Also chemophysical analysis and imaging demonstrate attachment of Ni-P with IF-WS₂ nanoparticles on stainless steel after extensive friction test. Kornfield et al design a nanocomposite of WS₂ and Poly(L-lactide) (PLLA) for bioresorbable vascular scaffolds (BVS). PLLA is first clinically approved polymer for BVS manufacturing and degrade to lactic acid which is non-toxic material for body and has so many applications in drug delivery, food packaging and biomedical devices. Although PLLA-based polymers have twice thickness than metal stents but they are fragile, so there is a need to reinforce their strength without adding to its thickness. WS₂ nanoparticles have excellent mechanical properties and flexibility and can increase PLLA strength. PLLA-WS₂ composites were prepared by addition 0.05wt% of WS₂ to PLLA and solvent casting then hot press method. Mechanical properties of composite was investigated by subjecting WS₂ to uniaxial stretching at 500mm/min stretching rate at 90 °C temperature. Up to 100% strain was shown in stress-strain profile of both nanocomposite and neat polymer. Spectroscopy analysis confirm WS₂ nanotubes act as nucleation center and increase crystallinity [49].

Aging is one the challenges that humans are faced and bone fractures especially due to osteoporosis is one big problem. Developing biocompatible material to use in bone tissue engineering is a solution, but most of them don't have adequate mechanical properties,

their degradation rate is uncontrolled and lack bioactivity, so there is an urge to produce better material. In TMDCs, tungsten disulfide (WS₂) has shown good biocompatibility, physical and photoelectrochemical properties. Chen et al. used chlorophyll molecules to synthesize WS₂ nanosheet with liquid-phase exfoliation method then mixed them with polycaprolactone (PCL)/calcium silicate (CS) to produce biocompatible composite. Chlorophyll assisted WS₂ synthesis shown better stability than chlorophyll-less exfoliated WS₂. WS₂/PCL/CS composite didn't show any toxicity and due to their macro-pore structure improve nutrient transportation, cell in-growth and leading to osteogenesis and angiogenesis. Compared to PCL/CS alone WS₂/PCL/CS exhibit an increase in young's module from 32 MPa to 145 MPa and enhancement in compression strength from 2 MPa to 6 MPa. In vivo bone regeneration study exhibit a 120% compared to commercially MTA material and 300% mechanical properties enhancement compared to PCL/CS and resulted that WS₂/PCL/CS is an excellent candidate in bone regeneration composites [50].

Lalwani et al. used 0.01-0.2 wt.% concentration of tungsten disulfide nanotubes (WSNTs) to reinforce poly(propylene fumarate) (PPF) composite and compared it to SWCNT and MWCNTs. WPPF improved mechanical properties compared to neat PPF in all concentrations compared to SWCNTs and MWCNTs. WSNTs showed notable enhancement in mechanical properties and high crosslinking density, uniformity and no aggregation while dispersed into polymer matrix compared to SWCNT and MWCNT which had micron sized aggregation in PPF matrix result in being excellent candidate for application in tissue engineering [51].

BIOCOMPATIBILITY OF WS₂ NM

Biocompatibility of Tungsten Disulfide Inorganic Nanotubes and Fullerene-Like Nanoparticles with Salivary Gland Cells. Impairment in salivary gland function lead to oral disease and there is no sufficient treatment for this disease. Aframian et al. investigate biocompatibility of WS₂ in Salivary gland cells. In research multiwall inorganic nanotube (INT-WS₂) and inorganic fullerene-like nanoparticles (IF-WS₂) were synthesized in high temperature using reactor. Toxicity of both groups were evaluated by A5 and RSC cells in different concentration 0.22 μ g/ml to 35.2 μ g/ml and 35.2 and 100 μ g/mL for

INT-WS₂ and IF-WS₂, respectively. Both cell line didn't show significant difference in kinetic, proliferation, viability and morphology also these particles were seen in cytoplasm of cell and not in nuclei with a membrane surrounding them indicate endocytosis mechanism of them, therefore this particles are biocompatible and can be used in medical applications [52].

WS₂ IN DRUG DELIVERY AND THERAPEUTIC AGENTS IN CANCER THERAPY

Preparation of stable and biocompatible nanomaterial and nanocomposite for drug delivery is a basic challenge in nanomedicine. Providing new safe nanomaterial with drug delivery capability is an important issue in medical nanotechnology. It seems that WS₂ related nanomaterial are suitable candidate for this purpose. Recently many research carried out about this subject.

Kasinathan et al. synthesis chitosan functionalized WS₂ nanocomposite implanted with ruthenium nanoparticles (CS/WS₂/Ru). Being biocompatible and non-toxic chitosan is an excellent candidate in drug delivery systems. On the other hand, due to small size and large surface area WS₂ can improve biological features of chitosan. Ruthenium is a part of noble metals have a wide range of medical applications from biosensing to pharmaceuticals. Due to being toxic to fungi, bacteria, and viruses, Ru is a good option to development of anti-pathogenesis drugs. In vitro cytotoxicity of CS/WS₂/Ru nanoparticles was investigated on Vero cells with different concentration. Results shown minimum toxicity which can be negligible and consider it non-toxic. Antibacterial activity of nanoparticles was studied on *B. subtilis*, *S. aureus* as Gram (+) and *K. pneumoniae*, *E. coli* as Gram (-) bacterial group via with different concentration of nanocomposite. Results indicate oxidative stress generated by chitosan functionalized WS₂ nanosheets play a vital role in antibacterial activity. It was observed that Ru enters the cytoplasm and interacts with protein and DNA, causing cell death. MCF-7 breast cancer cell line was chosen to investigate anticancer activity of CS/WS₂/Ru in different concentrations compared to control groups. In 100 µg/ml CS/WS₂/Ru nanocomposite showed higher cell inhibition. W⁺⁴ and Ru⁺³ positive charge play role in disruption of cell membrane and mitochondrial dysfunction, ROS production and oxidative stress act as pathway for cytotoxic

effect in cancer cells and prove anticancer activity of composite [53]. In another study Kasinathan et al. used CS/WS₂/Pd to investigate antibacterial and anticancer activity. Bacterial groups and cancer cell lines which were subjected to nanoparticles were the same as their previous study. Antibacterial of CS/WS₂/Pd nanostructure were tested on Gram (+) and Gram (-) bacterial groups and inhibition zone in 100 µg/ml concentration was assessed. Maximum inhibition was observed for *E. coli*. In vitro cytotoxicity of nanoparticles was evaluated on Vero cells with different concentration and shown negligible toxicity. Also, in 100 µg/ml CS/WS₂ and CS/WS₂/Pd nanomaterial showed 70.15% and 73.24% MCF7 cancer cell inhibition respectively. Consequence showed W⁺⁴ and Pd⁺ positive charge effectively attached to negative charge cell membrane and play a role in its destruction [20]. Gnatyuk et al investigate anticancer activity of WS₂ nanosheet on Lewis lung carcinoma cell. WS₂ nanoparticles didn't show any sign of toxicity to cancer cells in the day 1 of incubation but prolongation of this time up to 2 days result in a concentration-dependent decrease in cell viability more than 30% with maximum cytotoxic effect at nearly 2 µg/ml of WS₂ this was due to entering tumor cells or accumulate on their surface in longer period of incubation time [54]. Tamayo-Ramos et al investigate toxicity of three groups of commercially WS₂ on adenocarcinomic human alveolar basal epithelial cells (A549 cells) and *Saccharomyces cerevisiae*. WS₂-ACS-M with lateral size from 100 nm to 4 µm (microdispersion), WS₂-ACS-N with a range from 20-500 nm (nano dispersion) and WS₂-ACS-N-PW which is dry powder form. Aqueous dispersion contains 1T'-WS₂, 2H-WS₂, WO₃ and SO₂. A549 cells were subjected to different concentrations of nanoparticles to assess ROS generation in cells resulted in a low level of ROS in treated cells exhibiting no toxicity. Toxicity test on *S. cerevisiae* in 160 mg/L and 800 mg/L concentration was done. After 2h there was no sign of toxicity however, after 24 h there was a decrease in cell viability. In 160 mg/L treated *S. cerevisiae*, WS₂-ACS-M reduction was more significant compared to WS₂-ACS-N however in 800 mg/L concentration WS₂-ACS-N exhibit more decrease compared to WS₂-ACS-M. Same assessments were done on aqueous solution of WS₂, which was prepared by dry powder form and were able to show a similar toxicity effect on *S. cerevisiae* cells [55].

CONCLUSION & FUTURE PERSPECTIVE

The purpose of this review was to consolidate existing research information on the WS₂ based nanomaterial for application in various fields of nanomedicine. The obtained results show that WS₂ nanomaterial and related nanocomposites are biocompatible and can be a significant approach for the use in biosensor, bioimaging, dental and orthopedic implant, controllable drug delivery, tissue engineering, cancer therapy, Photothermal and Radiation Therapy. Considering the chemophysical structure, optical and electrical unique properties and wide potential of tungsten nanomaterial, these nanoparticles can be considered as a solution to overcome a lot of problems in the field of medicine and pharmaceuticals in the future. The other hand, better understanding of fundamental of WS₂ nanomaterial and their interaction with biomolecules and cell or organs, moreover functionalization of WS₂ NM by biomolecules could help researcher and medical scientist to developed the new nanostructures and nanocomposites with high efficient and applicable in nanomedicine in the future.

CONFLICT OF INTEREST

The authors declare no conflict of interest .

REFERENCES

- Salata OV (2004) Applications of nanoparticles in biology and medicine. *Journal of nanobiotechnology* 2, 1-6. <https://doi.org/10.1186/1477-3155-2-3>
- Włodarczyk R, Kwarciak-Kozłowska A (2021) Nanoparticles from the cosmetics and medical industries in legal and environmental aspects. *Sustainability* 13, 5805. <https://doi.org/10.3390/su13115805>
- Sim S, Wong NK (2021) Nanotechnology and its use in imaging and drug delivery. *Biomedical reports* 14, 1-9. <https://doi.org/10.3892/br.2021.1418>
- Cardoso VF, Francesko A, Ribeiro C, Bañobre-López M, Martins P, Lanceros-Mendez S (2018) Advances in magnetic nanoparticles for biomedical applications. *Advanced healthcare materials* 7, 1700845. <https://doi.org/10.1002/adhm.201700845>
- Yong Y, Cheng X, Bao T, Zu M, Yan L, Yin W, Ge C, Wang D ,et al (2015) Tungsten sulfide quantum dots as multifunctional nanotheranostics for in vivo dual-modal image-guided photothermal/radiotherapy synergistic therapy. *ACS nano* 9, 12451-63. <https://doi.org/10.1021/acsnano.5b05825>
- Levin T, Sade H, Binyamini RB-S, Pour M, Nachman I, Lellouche J-P (2019) Tungsten disulfide-based nanocomposites for photothermal therapy. *Beilstein journal of nanotechnology* 10, 811-22. <https://doi.org/10.3762/bjnano.10.81>
- Samadi M, Sarikhani N, Zirak M, Zhang H, Zhang H-L, Moshfegh AZ (2018) Group 6 transition metal dichalcogenide nanomaterials: synthesis, applications and future perspectives. *Nanoscale Horizons* 3, 90-204. <https://doi.org/10.1039/C7NH00137A>
- Eftekhari A (2017) Tungsten dichalcogenides (WS₂, WSe₂, and WTe₂): materials chemistry and applications. *Journal of Materials Chemistry A* 5, 18299-325. <https://doi.org/10.1039/C7TA04268J>
- Wilson JA, Yoffe A (1969) The transition metal dichalcogenides discussion and interpretation of the observed optical, electrical and structural properties. *Advances in Physics* 18, 193-335. <https://doi.org/10.1080/00018736900101307>
- Egorova KS, Ananikov VP (2017) Toxicity of metal compounds: knowledge and myths. *Organometallics* 36, 4071-90. <https://doi.org/10.1021/acs.organomet.7b00605>
- Kim S, Bark H, Nam S, Choi H, Lee H (2018) Control of Electrical and Thermal Transport Properties by Hybridization of Two-Dimensional Tungsten Disulfide and Reduced Graphene Oxide for Thermoelectric Applications. *ACS Sustainable Chemistry & Engineering* 6, 15487-93. <https://doi.org/10.1021/acssuschemeng.8b03949>
- Lopez-Urias F, Elias AL, Perea-Lopez N, Gutierrez HR, Terrones M, Terrones H (2014) Electronic, magnetic, optical, and edge-reactivity properties of semiconducting and metallic WS₂ nanoribbons. *2D Materials* 2, 015002. <https://doi.org/10.1088/2053-1583/2/1/015002>
- Ding J, Feng A, Li X, Ding S, Liu L, Ren W (2021) Properties, preparation, and application of tungsten disulfide: A review. *Journal of Physics D: Applied Physics* 54, 173002. <https://doi.org/10.1088/1361-6463/abd9e8>
- Mao X, Xu Y, Xue Q, Wang W, Gao D (2013) Ferromagnetism in exfoliated tungsten disulfide nanosheets. *Nanoscale research letters* 8, 1-6. <https://doi.org/10.1186/1556-276X-8-430>
- Nagaraju C, Gopi CVM, Ahn J-W, Kim H-J (2018) Hydrothermal synthesis of MoS₂ and WS₂ nanoparticles for high-performance supercapacitor applications. *New Journal of Chemistry* 42, 12357-60. <https://doi.org/10.1039/C8NJ02822B>
- Sinha SS, Yadgarov L, Aliev SB, Feldman Y, Pinkas I, Chithaiah P, Ghosh S, Idelevich A ,et al (2021) MoS₂ and WS₂ Nanotubes: Synthesis, Structural Elucidation, and Optical Characterization. *The Journal of Physical Chemistry C* 125, 6324-40. <https://doi.org/10.1021/acs.jpcc.0c10784>
- Zhang D, Liu T, Cheng J, Liang S, Chai J, Yang X, Wang H, Zheng G ,et al (2019) Controllable synthesis and characterization of tungsten disulfide nanosheets as promising nanomaterials for electronic devices. *Ceramics International* 45, 12443-8. <https://doi.org/10.1016/j.ceramint.2019.03.177>
- Pataniya PM, Late D, Sumesh C (2021) Photosensitive WS₂/ZnO nano-heterostructure-based electrocatalysts for hydrogen evolution reaction. *ACS Applied Energy Materials* 4, 755-62. <https://doi.org/10.1021/acsaem.0c02608>
- Tang M, Wu Y, Yang J, Wang H, Lin T, Xue Y (2021) Graphene/tungsten disulfide core-sheath fibers: high-performance electrodes for flexible all-solid-state fiber-shaped supercapacitors. *Journal of Alloys and Compounds* 858, 157747. <https://doi.org/10.1016/j.jallcom.2020.157747>
- Kasinathan K, Marimuthu K, Murugesan B, Samayanan S, Cai Y, Rathinam C (2021) Facile synthesis of highly biologically active chitosan functionalized 2D WS₂ nanocomposite anchored with palladium nanoparticles for antibacterial and anticancer activity: In-vitro biomedical

- evaluation. *Journal of Molecular Liquids* 335, 116582. <https://doi.org/10.1016/j.molliq.2021.116582>
21. Stejskal J, Acharya U, Bober P, Hajná M, Trchová M, Mičušík M, Omastová M, Pašti I, et al (2019) Surface modification of tungsten disulfide with polypyrrole for enhancement of the conductivity and its impact on hydrogen evolution reaction. *Applied Surface Science* 492, 497-503. <https://doi.org/10.1016/j.apsusc.2019.06.175>
 22. Li C, Bo X, Li M, Guo L (2017) Facile electrodeposition fabrication of molybdenum-tungsten sulfide on carbon cloth for electrocatalytic hydrogen evolution. *International Journal of Hydrogen Energy* 42, 15479-88. <https://doi.org/10.1016/j.ijhydene.2017.05.046>
 23. Basu S, Chakraborty A, Alkisiwani A-RI, Shamiya Y, Paul A (2022) Investigation of a 2D WS₂ nanosheet-reinforced tough DNA hydrogel as a biomedical scaffold: preparation and in vitro characterization. *Materials Advances* 3, 946-52. <https://doi.org/10.1039/D1MA00897H>
 24. Kissinger PT (2005) Biosensors-a perspective. *Biosensors and Bioelectronics* 20, 2512-6. <https://doi.org/10.1016/j.bios.2004.10.004>
 25. McNaught AD, Wilkinson A. *Compendium of chemical terminology*: Blackwell Science Oxford; 1997.
 26. Wu G, Zheng H, Xing Y, Wang C, Yuan X, Zhu X (2022) A sensitive electrochemical sensor for environmental toxicity monitoring based on tungsten disulfide nanosheets/hydroxylated carbon nanotubes nanocomposite. *Chemosphere* 286, 131602. <https://doi.org/10.1016/j.chemosphere.2021.131602>
 27. Wang L, Liang H, Xu M, Wang L, Xie Y, Song Y (2019) Ratiometric electrochemical biosensing based on double-enzymes loaded on two-dimensional dual-pore COFET-TA-TPAL. *Sensors and Actuators B: Chemical* 298, 126859. <https://doi.org/10.1016/j.snb.2019.126859>
 28. Su S, Sun Q, Gu X, Xu Y, Shen J, Zhu D, Chao J, Fan C, et al (2019) Two-dimensional nanomaterials for biosensing applications. *TrAC Trends in Analytical Chemistry* 119, 115610. <https://doi.org/10.1016/j.trac.2019.07.021>
 29. Malik P, Katyal V, Malik V, Asatkar A, Inwati G, Mukherjee TK (2013) Nanobiosensors: concepts and variations. *International Scholarly Research Notices* 2013. <https://doi.org/10.1155/2013/327435>
 30. Guo X, Wang Y, Wu F, Ni Y, Kokot S (2015) The use of tungsten disulfide dots as highly selective, fluorescent probes for analysis of nitrofurazone. *Talanta* 144, 1036-43. <https://doi.org/10.1016/j.talanta.2015.07.055>
 31. Wang P, Wang A, Hassan MM, Ouyang Q, Li H, Chen Q (2020) A highly sensitive upconversion nanoparticles-WS₂ nanosheet sensing platform for *Escherichia coli* detection. *Sensors and Actuators B: Chemical* 320, 128434. <https://doi.org/10.1016/j.snb.2020.128434>
 32. Huang K-J, Liu Y-J, Wang H-B, Gan T, Liu Y-M, Wang L-L (2014) Signal amplification for electrochemical DNA biosensor based on two-dimensional graphene analogue tungsten sulfide-graphene composites and gold nanoparticles. *Sensors and Actuators B: Chemical* 191, 828-36. <https://doi.org/10.1016/j.snb.2013.10.072>
 33. Irani-Nezhad MH, Jalili R, Kohan E, Khataee A, Yoon Y (2022) Tungsten disulfide (WS₂)/fluorescein ratiometric fluorescent probe for detection of cefixime residues in milk. *Environmental Research* 205, 112512. <https://doi.org/10.1016/j.envres.2021.112512>
 34. Pourakbari R, Yousefi M, Khalilzadeh B, Irani-nezhad MH, Khataee A, Aghebati-Maleki L, Soleimanian A, Kamrani A, et al (2022) Early stage evaluation of colon cancer using tungsten disulfide quantum dots and bacteriophage nano-biocomposite as an efficient electrochemical platform. *Cancer Nanotechnology* 13, 1-17. <https://doi.org/10.1186/s12645-022-00113-2>
 35. Garg M, Chatterjee M, Sharma AL, Singh S (2020) Label-free approach for electrochemical ferritin sensing using biosurfactant stabilized tungsten disulfide quantum dots. *Biosensors and Bioelectronics* 151, 111979. <https://doi.org/10.1016/j.bios.2019.111979>
 36. Wang Y, Gong C, Zhu Y, Wang Q, Geng L (2021) Signal-on electrochemical aptasensor for sensitive detection of sulfamethazine based on carbon quantum dots/tungsten disulfide nanocomposites. *Electrochimica Acta* 393, 139054. <https://doi.org/10.1016/j.electacta.2021.139054>
 37. Zhao X, He D, Wang Y, Fu C (2018) Facile fabrication of tungsten disulfide quantum dots (WS₂ QDs) as effective probes for fluorescence detection of dopamine (DA). *Materials Chemistry and Physics* 207, 130-4. <https://doi.org/10.1016/j.matchemphys.2017.12.045>
 38. Rahman MS, Hasan MR, Rikta KA, Anower M (2018) A novel graphene coated surface plasmon resonance biosensor with tungsten disulfide (WS₂) for sensing DNA hybridization. *Optical Materials* 75, 567-73. <https://doi.org/10.1016/j.optmat.2017.11.013>
 39. Adigilli HK, Pandey A, Joardar J (2020) 2D-Nanolayered Tungsten and Molybdenum Disulfides: Structure, Properties, Synthesis, and Processing for Strategic Applications. *Handbook of Advanced Ceramics and Composites: Defense, Security, Aerospace and Energy Applications* 75-120. https://doi.org/10.1007/978-3-030-16347-1_4
 40. Macutkevicius J, Belovickis J, Otorkest G, Dodiuk H, Kenig S, Samulionis V, Banys J, Zak A (2018) Broadband dielectric and ultrasonic properties of WS₂ nanotubes/polyurethane composites. *Polymer Composites* 39, 4477-85. <https://doi.org/10.1002/pc.24554>
 41. Li X, Pan Z, Li Z, Wang X, Saravanakumar B, Zhong Y, Xing L, Xu M, et al (2019) Coral-like reduced graphene oxide/tungsten sulfide hybrid as a cathode host of high performance lithium-sulfur battery. *Journal of Power Sources* 420, 22-8. <https://doi.org/10.1016/j.jpowsour.2019.02.089>
 42. Vattikuti SVP, Nagajothi PC, Devarayapalli KC, Shim J (2020) Depositing reduced graphene oxide onto tungsten disulfide nanosheets via microwave irradiation: confirmation of four-electron transfer-assisted oxygen reduction and methanol oxidation reaction. *New Journal of Chemistry* 44, 10638-47. <https://doi.org/10.1039/D0NJ01097A>
 43. De Stefani A, Bruno G, Preo G, Gracco A (2020) Application of nanotechnology in orthodontic materials: a state-of-the-art review. *Dentistry journal* 8, 126. <https://doi.org/10.3390/dj8040126>
 44. Wang Y, Song S, Lu T, Cheng Y, Song Y, Wang S, Tan F, Li J, et al (2019) Oxygen-supplementing mesoporous polydopamine nanosponges with WS₂ QDs-embedded for CT/MSOT/MR imaging and thermoradiotherapy of hypoxic cancer. *Biomaterials* 220, 119405. <https://doi.org/10.1016/j.biomaterials.2019.119405>
 45. Wang J-T, Zhang W, Wang W-B, Wu Y-J, Zhou L, Cao F (2019) One-pot bottom-up fabrication of biocompatible PEGylated WS₂ nanoparticles for CT-guided photothermal therapy of tumors in vivo. *Biochemical*

- and biophysical research communications 511, 587-91. <https://doi.org/10.1016/j.bbrc.2019.01.009>
46. Hsiao PF, Anbazhagan R, Tsai H-C, Lin S-J, Lin S-Y, Lee K-Y, Kao C-Y, Chen R-S ,et al (2020) Fabrication of electroactive polypyrrole-tungsten disulfide nanocomposite for enhanced in vivo drug release in mice skin. *Materials Science and Engineering: C* 107, 110330. <https://doi.org/10.1016/j.msec.2019.110330>
 47. Sobhani M, Zieglari A, Moniri E, Panahi HA, Asli MD (2021) Graft hyper-branched dendrimer onto WS2 nanosheets modified Poly (N-Vinylcaprolactam) as a thermosensitive nanocarrier for Pioglitazone delivery using near-infrared radiation. *International Journal of Pharmaceutics* 607, 120985. <https://doi.org/10.1016/j.ijpharm.2021.120985>
 48. Gracco A, Dandrea M, Deflorian F, Zanella C, De Stefani A, Bruno G, Stellini E (2019) Application of a molybdenum and tungsten disulfide coating to improve tribological properties of orthodontic archwires. *Nanomaterials* 9, 753. <https://doi.org/10.3390/nano9050753>
 49. Tammaro L, Di Luccio T, Borriello C, Loffredo F, Ramachandran K, Villani F, Di Benedetto F, Schiller T ,et al editors. Effect of tungsten disulfide (WS2) nanotubes on structural, morphological and mechanical properties of poly (L-lactide)(PLLA) films. *AIP Conference Proceedings*; 2018: AIP Publishing LLC. <https://doi.org/10.1063/1.5045935>
 50. Chen Y-W, Shie M-Y, Hsiao C-H, Liang Y-C, Wang B, Chen I, Peter W (2020) Synthesis of high-quality monolayer tungsten disulfide with chlorophylls and its application for enhancing bone regeneration. *npj 2D Materials and Applications* 4, 1-9. <https://doi.org/10.1038/s41699-020-00168-y>
 51. Lalwani G, Henslee AM, Farshid B, Parmar P, Lin L, Qin Y-X, Kasper FK, Mikos AG ,et al (2013) Tungsten disulfide nanotubes reinforced biodegradable polymers for bone tissue engineering. *Acta biomaterialia* 9, 8365-73. <https://doi.org/10.1016/j.actbio.2013.05.018>
 52. Goldman EB, Zak A, Tenne R, Kartvelishvili E, Levin-Zaidman S, Neumann Y, Stiubea-Cohen R, Palmon A ,et al (2015) Biocompatibility of tungsten disulfide inorganic nanotubes and fullerene-like nanoparticles with salivary gland cells. *Tissue Engineering Part A* 21, 1013-23. <https://doi.org/10.1089/ten.tea.2014.0163>
 53. Kasinathan K, Marimuthu K, Murugesan B, Sathiaiah M, Subramanian P, Sivakumar P, Swaminathan U, Subbiah R (2021) Fabrication of eco-friendly chitosan functionalized few-layered WS2 nanocomposite implanted with ruthenium nanoparticles for in vitro antibacterial and anticancer activity: Synthesis, characterization, and pharmaceutical applications. *International Journal of Biological Macromolecules* 190, 520-32. <https://doi.org/10.1016/j.ijbiomac.2021.08.153>
 54. Kolesnik D, Pyaskovskaya O, Gnatyuk O, Cherepanov V, Karakhim S, Polovii I, Posudievsky OY, Konoshchuk N, et al (2021) The effect of 2D tungsten disulfide nanoparticles on Lewis lung carcinoma cells in vitro. *RSC advances* 11, 16142-50. <https://doi.org/10.1039/D1RA01469B>
 55. Domi B, Bhorkar K, Rumbo C, Sygellou L, Martin SM, Quesada R, Yannopoulos SN, Tamayo-Ramos JA (2021) Toxicological assessment of commercial monolayer tungsten disulfide nanomaterials aqueous suspensions using human A549 cells and the model fungus *Saccharomyces cerevisiae*. *Chemosphere* 272, 129603. <https://doi.org/10.1016/j.chemosphere.2021.129603>